

NACA TN No. 1465

NATIONAL ADVISORY COMMITTEE FOR AERONAUTICS

TECHNICAL NOTE

No. 1465

THE RUPTURE-TEST CHARACTERISTICS OF HEAT-RESISTANT
SHEET ALLOYS AT 1700° AND 1800° F


By J. W. Freeman, E. E. Reynolds, and A. E. White

University of Michigan



Washington

February 1948

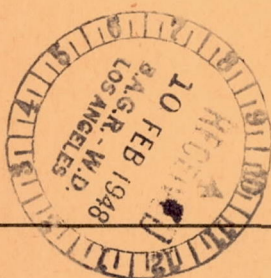

TECHNICAL LIBRARY
AIRESEARCH MANUFACTURING CO.
9851-9951 SEPULVEDA BLVD.
INGLEWOOD
CALIFORNIA



NATIONAL ADVISORY COMMITTEE FOR AERONAUTICS

TECHNICAL NOTE NO. 1465

THE RUPTURE-TEST CHARACTERISTICS OF HEAT-RESISTANT SHEET ALLOYS

AT 1700° AND 1800° F

By J. W. Freeman, E. E. Reynolds, and A. E. White

SUMMARY

The characteristics of a representative group of heat-resistant alloys in sheet form were investigated by rupture tests at 1700° and 1800° F. The primary purpose was to provide data which could be used by the aircraft industry to determine whether the rupture-test properties of an alloy would be a criterion of service performance in combustion chambers and other applications of sheet alloys at high temperatures in power plants for aircraft. Suitable service data were not available for this type of correlation in the present report.

The materials studied included the standard chromium-nickel types 330 (35Ni-15Cr), 310 (25Cr-20Ni), 310S (25Cr-20Ni+Si), 309 (25Cr-12Ni), and Inconel alloys, the new highly alloyed materials known as Vitallium, Co-Cr-Ni, S816, S590, and low-carbon N-155, and four experimental alloys containing cobalt, molybdenum, tungsten, and boron in addition to nickel and chromium. The highly alloyed materials, in most cases, had higher rupture strengths only for time periods up to about 1000 hours at 1700° F and for somewhat shorter time periods at 1800° F. The relative rupture strengths varied with the time period and the temperature considered. In general, Vitallium, J-838, and S-590 were the strongest of the new alloys and type 310S was the best of the standard alloys. Low-carbon N-155 apparently had the best strength at time periods of 1000 hours and longer.

The rupture strengths at 1700° F ranged up to 12,000, 8000, 5200, and 3900 psi for fracture in 10, 100, 400, and 1000 hours, respectively. The corresponding range in rupture strengths at 1800° F was up to 8600, 4200, 2500, and 2000 psi.

Rather wide differences in properties of separate heats of type 310S and Inconel alloys showed that treatment prior to testing influenced the rupture-test characteristics. The apparent equalization of rupture strengths at the longer time periods was attributed to agglomeration, solution, or lack of precipitation of the excess constituents believed to impart high rupture strength to some of the alloys at lower temperatures. Apparently the strengths of the various matrix materials were not greatly different. Service conditions under which corrosion would differ from that during the rupture tests would result in different rupture properties. Presumably a less-oxidizing condition would improve the performance by some of the alloys.

INTRODUCTION

One of the difficulties encountered in the operation of gas turbines has been the short life of liners for combustion chambers. A suitable metallurgical test which would give results correlating with service performance was not available. It was suggested that the rupture test might fulfill the need.

Accordingly, an investigation of the characteristics of a representative group of alloys was conducted to provide rupture strength and ductility data. Fourteen alloys in the form of 0.031-inch-thick sheet were used. A number of these were obtained from commercial production and the others were experimental alloys. The range of service temperatures was estimated at 1700° to 1800° F and the tests were confined to these temperatures.

Suitable data were not available during preparation of this report to correlate the performance of the alloys in service with the rupture-test characteristics. In an evaluation of the test and the alloys, due consideration should be given to the possibility that the data may not be typical for some of the alloys. There is reason to believe that the rupture-test characteristics vary to a considerable extent, depending on the prior treatment during manufacturing for any one alloy. The influence of this factor has not been determined for sheet alloys.

The investigation was conducted under the sponsorship and with the financial assistance of the National Advisory Committee for Aeronautics as a part of their program of sponsored research at the Department of Engineering Research of the University of Michigan on heat-resisting alloys for gas turbines. The program has covered extensive work on rotor materials and is being continued in this field and in the field of sheet alloys for combustion chambers and other high-temperature-duct work.

TEST MATERIALS

Fourteen alloys, the chemical compositions of which are shown in table I, were considered in the investigation. Five of these, types 330, 310, 310S, 309, and Inconel are well known chromium-nickel-iron alloys which have been used widely for heat-resisting applications for a number of years. Five of the alloys, Vitallium, Co-Cr-Ni, S816, S590, and low-carbon N-155 are relatively new alloys containing large amounts of cobalt, chromium, and nickel, along with additions of tungsten, molybdenum, or columbium. The four alloys, J-837, J-838, J-839, and J-840, were new experimental alloys.

Two separate lots of Inconel and type 310S alloys were included. This was done primarily to obtain some measure of the degree to which the data reported are typical. The particular alloys were selected because they were of special interest for combustion liners and other high-temperature-duct work in gas turbines.

All the test materials were supplied in a condition in which they ordinarily would be furnished commercially for high-temperature service. Possible exceptions are that this might be altered by further experience with the new highly alloyed materials and the four experimental heats. In fact, six of the alloys were obtained from a consumer who had purchased the materials for the construction of combustion chambers.

The materials were supplied as strips 22 inches long, $1\frac{1}{4}$ inches wide, and 0.030 to 0.040 inch thick. The width in the 2-inch gage test section was reduced to 1 inch and the specimens were tested as such. The available details of processing and heat treatment are summarized as follows:

Vitallium:

The material tested was from Crucible melts. Ingots were forged between 2040° F and 1900° F. Rolling of the hammered slabs was done from 2100° to 1900° F. After finish rolling, the pieces were annealed 6 minutes at 2050° F and pickled. This material was furnished by the General Electric Company.

Co-Cr-Ni:

The sheets were hot-rolled with a finishing temperature of 2100° to 2125° F and then annealed by heating at 2175° to 2200° F. In the annealing process, the material was held in the furnace just long enough to reach a required temperature and then air-cooled. The Haynes Stellite Company made the sheets, and the specimens were furnished by the General Electric Company.

S816:

Sheets were hot-rolled to 0.035-inch gage at 2200° to 2250° F, annealed at 2200° to 2250° F for 5 minutes and air-cooled. The material was then sand-blasted, scrubbed, given two passes on cold rolls, and buckled. It was made by the Allegheny-Ludlum Steel Corporation and furnished by the General Electric Company.

S590:

The final processing included annealing at 2150° F with an air cool. The sheets were then sand-blasted, acid-dipped, scrubbed, and buckled. The samples were made and supplied by the Allegheny-Ludlum Steel Corporation.

Inconel:

The materials designated as Inconel-1 and Inconel-2 were hot-rolled with a final rolling temperature of 2100° F and annealed at 1900° F, followed by a pickle. Sheets were processed by the International Nickel Company. Tests on Inconel-2 were made from a single sheet.

Low-carbon N-155, J-837, J-838, J-839, and J-840 alloys:

Ingots from a 30-pound induction furnace heat were hot-forged to sheet bars approximately 2 inches wide by 1 inch thick, and the bars were rolled to strips. Forging was from approximately 2100° to nearly 1500° F. The sheets were rolled from approximately 2000° to nearly 1400° F. Samples were then annealed at 2000° to 2100° F and air-cooled. These alloys were made and supplied by the Union Carbide and Carbon Research Laboratories, Inc.

Type 330:

Sheets were hot-rolled from a large induction heat, annealed at 1950° F, air-cooled, and pickled. The Crucible Steel Company made and supplied the specimens.

Type 310:

The Crucible Steel Company fabricated and supplied specimens from a large induction heat. The sheets were hot-rolled, annealed at 2050° F, air-cooled, and pickled.

Type 310S:

The material designated AF-18 was hot-rolled to 0.045-inch gage sheet from 2100° F, annealed for 6 to 8 minutes at 2100° to 2150° F and air-cooled, sand-blasted, spot-ground, cold-rolled to 0.033-inch gage, annealed 2100° to 2150° F for 6 to 8 minutes and air-cooled, sand-blasted, scrubbed, cold-rolled one pass, and buckled. This alloy was made by the Allegheny-Ludlum Steel Corporation and supplied by the General Electric Company.

The material from heat 14626 was hot-rolled to 0.050-inch gage sheet, pickled, annealed at 2180° F for 6 minutes, water-quenched, sand-blasted, scrubbed, cold-rolled to 0.040 inch, annealed 2180° F for 6 minutes, water-quenched, sand-blasted, scrubbed, cold-rolled one pass to flatten, roller-leveled, and sheared. This alloy was made and supplied by the Allegheny-Ludlum Steel Corporation.

Type 309:

No processing information is available for this material. Presumably it was hot-rolled and annealed. It was furnished by the General Electric Company.

PROCEDURE

This investigation of sheet materials included sufficient tests to evaluate the rupture properties at 1700° and 1800° F from 1 hour to at

least 400 hours. The alloys were examined metallographically before and after rupture testing.

The short-time tensile tests were run on those alloys for which a sufficient number of specimens were supplied. The tensile machine was operated at a head speed of 0.03 inch per minute after holding the specimen at the test temperature for 1 hour. No strain data were obtained during these tests. Rupture tests of less than 10-hour duration were also conducted in the tensile machine after holding the specimen for 1 hour at temperature.

The longer-time rupture tests were run in single-specimen units. The specimens were held approximately 24 hours at the required temperature prior to application of the load. Direct loading was used to apply the stress to the lower-stress tests. The higher stressed specimens were loaded by a simple beam through a system of knife edges. No time-elongation data were obtained from the rupture tests because of the difficulty of making reliable measurements on thin sheets, particularly at these temperatures.

Metallographic samples of the cross section, taken lengthwise of the strips and including the fracture of the rupture specimens from the longest duration tests at each temperature, were polished, etched, and photographed at magnifications of 100X and 1000X.

RESULTS

The data from the rupture and tensile tests are given in table II. The usual logarithmic curves of stress against rupture time are shown in figure 1. The relative rupture strengths (obtained from fig. 1) and ductility varied with both the time period and the temperature, as is shown by the tabulation of rupture strengths and estimated ductility in tables III and IV and their graphical comparison in figure 2.

A tendency toward erratic results was characteristic of some of the materials. In some cases these stress-rupture time curves (fig. 1) showed abrupt changes in slope. The curves for type 330 at 1700° F and J-840 at 1800° F showed an unusual characteristic in that they had a lower slope at longer time periods.

The stress for rupture in 100 hours varied from 1950 to 8000 psi at 1700° F and 2200 to 4200 psi at 1800° F. In general, Vitallium, J-838, S590, and low-carbon N-155 had the highest rupture strengths. Type 330 was the weakest at 1700° F; whereas, Inconel and type 309 were only slightly stronger. The weaker alloys at 1700° F were not tested at 1800° F. Of those tested at 1800° F, S816 had the lowest strengths for time periods longer than 100 hours.

The degree of ductility to fracture in the rupture tests varied to a considerable extent between alloys. Of the alloys with the highest rupture strengths, J-838 had the highest elongation, although the others also had good ductility. Low elongation was exhibited by Co-Cr-Ni and type 310S alloys.

The low-nickel alloys J-837 and J-839 were subject to rapid oxidation and failed from this cause in the rupture tests. The loss in section size due to oxidation was of such influence that it was not possible to obtain the usual stress-rupture time curves. The low oxidation resistance for these two alloys was verified by heating small samples without stress at 1700° F and obtaining complete oxidation in 100 hours.

The original materials and the fractured rupture specimens from the most prolonged tests were examined metallographically. The information obtained is illustrated by the photomicrographs of figures 3 to 15 and is summarized as follows:

(1) There was no appreciable tendency for grain growth in any of the alloys during rupture testing. There was, however, considerable variation in grain size between individual alloys.

(2) A layer of clear structure was observed at the surface of the rupture specimens of all the alloys. This was probably the result of decarburization or a loss of other alloying elements by a similar mechanism.

(3) Agglomeration of the excess constituent occurred during rupture testing in most of the materials. This was accompanied by further precipitation in Co-Cr-Ni and type 310S alloys. These were also the only two alloys in which intergranular precipitation occurred.

(4) There was a considerable degree of difference in the amount of intergranular cracking which occurred near the fracture of the various materials and in the amount of oxidation that occurred in these cracks. Inconel, in particular, was very susceptible to intergranular oxidation.

DISCUSSION OF RESULTS

The primary purpose of this investigation was to provide rupture-test data for a representative group of alloys which might be used for combustion-chamber liners and other high-temperature applications for sheet materials in power plants for aircraft. Data at 1700° and 1800° F are presented for several of the standard chromium-nickel alloys, some of the newer, highly alloyed materials, and some new experimental modifications.

The newer alloys were, in general, outstandingly stronger than the standard chromium-nickel alloys only at 1700° F. This degree of superiority decreased as the time for rupture increased. The same general

trends existed at 1800° F, where the time period for equalizing rupture strengths was less than at 1700° F. One heat of the standard chromium-nickel alloy, type 310S with 0.13 percent carbon, had considerably higher rupture strengths than the other standard alloys. This particular heat compared quite favorably in strength with the new, highly alloyed materials. One heat of Inconel alloy had an exceptionally high 1000-hour strength at 1800° F. One of the more highly alloyed materials, S816, seemed to have abnormally low strength.

Other factors than chemical composition certainly influenced the variations in strength between the alloys. The differences in rupture strength between the two heats of type 310S and between the two lots of Inconel suggest that processing procedure and heat treatment had a pronounced influence on the results. Oxidation probably influenced the results as was indicated by the tests of Inconel, J-837, and J-839 alloys.

The possible effects of processing procedure and heat treatment may be appraised by the comparison of data in table V for the alloys in sheet, bar stock, and cast forms. A rather wide range in strength has been obtained for each alloy. In general, the cast form had the highest strength, the bar stock intermediate, and the sheet form lowest. There were, however, exceptions, depending on the heat treatment of the bar stock. For instance, low-carbon N-155 in the hot-rolled condition and types 309 and 310 with lower-temperature heat treatments were weaker than the sheet materials.

Oxidation undoubtedly influenced the results. This influence may have taken place in two ways. One is that some alloys, such as type 310S, had better strength because of high resistance to oxidation. At the opposite extreme were J-837 and J-839, which failed primarily by oxidation. The other possible effect would be that part of the low strength of sheet materials in comparison with bar stock was due to a larger surface area per unit of cross section exposed to oxidation than in the round specimens from bar stock.

A recent study of the results of rupture tests of standard chromium-nickel alloys at temperatures up to 1800° F suggested that nitrogen contamination, as well as oxidation, might have influenced the results of this investigation. (See reference 3.) In reference 3, nitrogen contents as high as 1.33 percent were observed after rupture tests at 1800° F on 25Cr-20Ni steel. The microstructures of the type 310 and type 310S sheet samples suggested the possibility of a nitrogen pickup in this investigation. Accordingly several samples were analyzed for nitrogen with the following results:

| Alloy | Test conditions | | | Nitrogen content near fracture (percent) |
|-------------------|------------------|--------------|-------------------|--|
| | Temperature (°F) | Stress (psi) | Rupture time (hr) | |
| S816 | 1800 | 1500 | 260 | 0.27 |
| Type 330 | 1700 | 1500 | 811 | .23 |
| Type 310 | 1700 | 2500 | 728 | .19 |
| Type 310S | 1700 | 3000 | 1124 | .26 |
| (AF-18) | 1800 | 2200 | 384 | .22 |
| Type 310S (14626) | 1700 | 2400 | 397 | .12 |

While the nitrogen contents of the original test materials were not available for comparison, certainly these results do not indicate the pronounced nitrogen pickup shown by reference 3. Sampling may have influenced these results, however, because reference 3 reported the nitrogen content to be highest at fracture of the specimens. There may have been undue dilution of the metal adjacent to the fractures in the sheet samples in order to obtain a sufficiently large sample for the analysis. Nitrogen pickup may therefore have been a larger influence on the results of the rupture tests in this investigation than is indicated by the foregoing analyses.

The primary reason why the newer alloys lost their superiority at longer time periods and in less time at 1800° F than at 1700° F was probably structural instability. These alloys are believed to derive their high strength at lower temperatures from precipitation of complex compounds. The microstructures of the samples indicate that these complex compounds agglomerate, redissolve, or do not precipitate at 1700° and 1800° F. Consequently, the strengthening effect from these particles, which is normal at lower temperatures, is lost or does not occur. The decarburization, or other alloy loss from the surface of the specimens, is another structural instability that may, in general, have adversely affected strength in the rupture test.

In summarization, then, it appears that the properties obtained from the rupture tests are dependent on strength of the matrix material, prior heat treatment, structural stability, and surface stability of the alloys under the test conditions. It follows that the properties might be considerably different under conditions in which the surface attack would be different from the air atmosphere of the tests. It might well be that a combustion-gas atmosphere with reducing characteristics would considerably increase the load-carrying ability.

The behavior of some of the alloys in the tests are specific examples of the general cases previously discussed. For example:

(1) Inconel appeared to be particularly susceptible to intergranular oxidation under the test conditions. (See fig. 7.) This oxidation was apparently more severe during testing at 1700° than at 1800° F. The erratic rupture time periods at 1700° F and the indication of equal strengths at 1700° and 1800° F for long time periods were probably due to oxidation rather than alloy strength controlling the time for rupture. The similarity of microstructure of both heats also indicates that oxidation rather than alloy strength controlled the rupture times.

(2) The low ductility of Co-Cr-Ni and type 310S alloys was associated with structural instability of the intergranular precipitation type. (See figs. 4, 13, and 14.) Apparently the nearly continuous envelopes of excess constituents which developed in the grain boundaries caused some brittleness. These were also the only alloys in which an appreciable amount of precipitation occurred during the tests.

(3) The structures of the type 310S samples, especially heat 14626 at 1700° F, were unusual in that the shape and the distribution of excess constituents were quite different from the other materials. (See fig. 14.) The amount of these constituents also seems greater than would be anticipated on the basis of the reported analyses.

(4) In type 310 alloy an easily etched constituent formed in the grain boundaries, but not in a continuous network. (See fig. 12.) Either this constituent does not cause brittleness or its discontinuous nature does not interfere with ductility at 1700° F.

(5) The structures of the more highly alloyed materials S816, S590, low-carbon N-155, J-838, and J-840, were quite similar. (See figs. 5, 6, 8, 9, and 10.) Testing caused relatively little change in the structures, although varying amounts of oxidation and intergranular cracking occurred. There was some indication that S816 underwent more structural alteration and oxidation than the other alloys of this group. The structure of the Vitallium sheet was comparable with these alloys, although both the grain size and the size of the excess constituent particles were larger. (See fig. 3.)

(6) All the alloys were subject to intergranular cracking during the rupture tests. No consistent relation, however, between this phenomenon and properties of the alloys could be observed.

The solution effects for the various annealing treatments varied to a considerable extent. Complete solution resulted in type 310S (heat 14626) and type 309. Either the temperature was too low, or insufficient time was allowed to dissolve carbides in Co-Cr-Ni, type 310, the AF-18 specimens of type 310S, and type 330 alloys. The newer materials with the higher alloy contents contained large particles of excess constituents which made it difficult to judge the relative solution effects. These particles apparently acted to maintain a fine grain size during annealing.

Most experience with the behavior of materials at high temperatures has indicated that at the higher temperatures a larger grain size gives higher strength than a fine grain size. The two heats of type 310S had different grain sizes. The finer-grained material, AF-18, however, had the higher strength. The usual effect of grain size may have been masked by the previously described complex structural changes in these alloys.

There are several factors which influence the properties of the alloys considered in this investigation. For this reason, there is a reasonable doubt whether the variations in properties which seemingly are due to chemical composition are due to this cause alone. For instance:

(1) The difference in structural characteristics between the two heats of type 310S suggests that heat treatment, instead of the variation in carbon content, may have been responsible for the difference in strengths.

(2) Apparently the higher cobalt of S816 in comparison with S590 was responsible for lower strength. The comparative data for bar stock and castings in table V indicate, however, that S590 is not universally better and that some other factor is also influencing the results. The description of the fabrication of these two alloys suggests that the S816 sheets were cold-worked after the final anneal, which would increase structural instability under the testing conditions. The relative effectiveness of heat treatments or differences in chromium content may also have been factors that influenced the rupture properties.

(3) In alloys J-837, J-838, J-839, and J-840 it appears that the lower nickel content of J-837 and J-839 was responsible for low oxidation resistance. The indication that the higher nitrogen content of J-840 in comparison with J-838 was detrimental to high-temperature properties should be checked on other heats before it is accepted as the controlling factor.

(4) In some cases there was remarkably little difference in rupture properties of alloys with rather specific variations in composition. For instance J-838 and J-840 differed from S590 in that they did not contain the 4 percent of columbium of S590 and their nickel content was 5 percent less. Boron was also added to J-838 and J-840, yet their rupture properties were similar.

CONCLUSIONS

Rupture tests conducted at 1700° and 1800° F on a representative group of alloys in sheet form led to the following conclusions:

1. The degree of superiority of the highly alloyed new materials over the standard chromium-nickel-iron alloys decreases with time for rupture at 1700° F, so that at time periods in excess of 1000 hours there are only relatively small differences. At 1800° F the time period for near equalization of strengths is considerably less than at 1700° F.

2. Sheet Vitallium, S590, low-carbon N-155, and J-838 alloys gave the highest strengths for most of the time periods considered. Type 310S was the best of the standard alloys.

3. Separate lots of type 310S and Inconel alloys in sheet form had quite widely varying properties, suggesting that prior heat treatment is of considerable influence on the properties. This was substantiated by data from other investigations.

4. Oxidation during the tests influenced the rupture test characteristics, indicating that the properties might depend considerably on the corrosion conditions during service. Less oxidizing conditions would probably increase rupture strength.

5. The tendency toward equalization of rupture strengths, regardless of alloy content, appears to be due to agglomeration, solution, or lack of precipitation of the excess constituent believed to control strength at lower temperatures.

Department of Engineering Research
University of Michigan
Ann Arbor, Mich., August 26, 1946

REFERENCES

1. Freeman, J. W., Reynolds, E. E., and White, A. E.: The Rupture Test Characteristics of Six Precision-Cast and Three Wrought Alloys at 1700° and 1800° F. NACA ARR No. 5J16, 1945.
2. Anon.: Resumé of High Temperature Investigations Conducted during 1945. The Timken Roller Bearing Co., Steel and Tube Div., (Canton, Ohio).
3. Anon.: Resumé of High Temperature Investigations Conducted during 1946-47. The Timken Roller Bearing Co., Steel and Tube Div., (Canton, Ohio).

TABLE I

12

CHEMICAL COMPOSITION OF SHEET ALLOYS TESTED AT 1700° AND 1800° F

| Alloy | Heat number | Chemical Composition (percent) | | | | | | | | | | | | | |
|-------------------|-------------|-----------------------------------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|----------------|-------|
| | | C | Mn | Si | P | S | Cr | Ni | Co | Mo | W | Cb | Fe | N ₂ | B |
| Vitallium | ----- | 0.20 | ----- | ----- | ----- | ----- | 27 | 2.5 | Bal. | 5.5 | ----- | ----- | ----- | ----- | ----- |
| Co-Cr-Ni | ----- | Low | ----- | ----- | ----- | ----- | 30 | 15 | 55 | ----- | ----- | ----- | ----- | ----- | ----- |
| S816 | ----- | .35 | ----- | ----- | ----- | ----- | 18 | 20 | 45 | 4 | 4 | 3 | ----- | ----- | ----- |
| S590 | ----- | .41 | 0.75 | 0.55 | ----- | ----- | 19.22 | 18.87 | 20.56 | 4.26 | 4.12 | 3.70 | Bal. | ----- | ----- |
| Inconel | ----- | .13 | 1 | .5 | ----- | ----- | 13 | 75 | ----- | ----- | ----- | ----- | 9 | ----- | ----- |
| Low-carbon N-155 | ----- | .14 | 1.48 | .58 | ----- | ----- | 21.24 | 19.53 | 20.22 | 3.10 | 1.95 | 1.01 | Bal. | 0.13 | ----- |
| J-837 | J-837 | .13 | 1.69 | .50 | ----- | ----- | 20.27 | 4.40 | 20.82 | 4.35 | 4.56 | ----- | Bal. | ----- | 0.34 |
| J-838 | J-838 | .11 | 1.46 | .51 | ----- | ----- | 20.30 | 14.90 | 21.14 | 4.35 | 4.43 | ----- | Bal. | ----- | .37 |
| J-839 | J-839 | .12 | 1.43 | .49 | ----- | ----- | 21.70 | 4.40 | 20.04 | 4.48 | 4.40 | ----- | Bal. | .124 | .56 |
| J-840 | J-840 | .13 | 1.38 | .58 | ----- | ----- | 21.29 | 15.28 | 20.98 | 4.33 | 4.33 | ----- | Bal. | .117 | .45 |
| Type 330 | 8R1445 | .18 | 1.37 | .62 | 0.015 | 0.018 | 15.77 | 33.27 | ----- | ----- | ----- | ----- | Bal. | ----- | ----- |
| Type 310 | 9R826 | .14 | 1.63 | 1.09 | .018 | .017 | 25.50 | 21.33 | ----- | ----- | ----- | ----- | Bal. | ----- | ----- |
| Type 310S (AF-18) | ----- | .13 | ----- | 2 | ----- | ----- | 25. | 20 | ----- | ----- | ----- | ----- | Bal. | ----- | ----- |
| Type 310S | 14626 | .047 | 1.92 | 2.27 | .023 | .008 | 24.83 | 20.49 | ----- | ----- | ----- | ----- | Bal. | ----- | ----- |
| Type 309 | ----- | .12 | ----- | ----- | ----- | ----- | 25 | 12 | ----- | ----- | ----- | ----- | Bal. | ----- | ----- |




TABLE II

RUPTURE-TEST DATA AT 1700° AND 1800° F FOR 14 SHEET ALLOYS

| Alloy | Temperature (°F) | Stress (psi) | Rupture time (hr) | Elongation (percent) |
|-----------|---------------------|-----------------|-----------------------|-------------------------|
| Vitallium | 1700 | 25,300 | ^a S.T.T.T. | 13 |
| | | 21,000 | 0.50 | 15 |
| | | 9,000 | 56 | 7 |
| | | 8,000 | 103 | 14 |
| | | 6,000 | 209 | 14 |
| | | 4,000 | 599 | 20 |
| Vitallium | 1800 | 18,900 | S.T.T.T. | 25 |
| | | 11,000 | 2.43 | 15 |
| | | 5,000 | 60 | 16 |
| | | 4,000 | 75 | 15 |
| | | 3,500 | 160 | 15 |
| | | 3,000 | 472 | 23 |
| Co-Cr-Ni | 1700 | 2,750 | 269 | 12 |
| | | 22,000 | S.T.T.T. | 6 |
| | | 13,000 | 1.13 | 4 |
| | | 10,000 | 16 | 9 |
| | | 6,000 | 52 | 2 |
| | | 5,000 | 140 | 1.5 |
| Co-Cr-Ni | 1800 | 4,000 | 333.5 | 3 |
| | | 16,000 | S.T.T.T. | 9 |
| | | 11,000 | 1.92 | 11 |
| | | 9,000 | 5.5 | 8 |
| | | 8,000 | 18 | 13 |
| | | 4,500 | 82 | 5 |
| S816 | 1700 | 4,000 | 90.5 | 4 |
| | | 3,500 | 192 | 6 |
| | | 3,000 | 132.5 | 3 |
| | | 2,500 | 324 | 2 |
| | | 26,200 | S.T.T.T. | 13 |
| | | 20,000 | 0.50 | 12 |
| | | 14,000 | 4.67 | 19 |
| | | 5,500 | 64 | 26 |
| | | 3,800 | 113 | 16 |
| | | 3,000 | 256.5 | 19 |
| | | 2,500 | 600 | 40 |

NACA

^a Short-time tensile test.

TABLE II - Continued

RUPTURE-TEST DATA AT 1700° AND 1800° F - Continued

| Alloy | Temperature (F) | Stress (psi) | Rupture time (hr) | Elongation (percent) |
|-----------|---------------------|-----------------|----------------------|-------------------------|
| S816 | 1800 | 18,000 | S.T.T.T | 26 |
| | | 9,000 | 3.20 | 30 |
| | | 3,500 | 25.5 | 32 |
| | | 2,500 | 83 | 36 |
| | | 2,000 | 136 | 39 |
| | | 1,500 | 259.5 | 45 |
| S590 | 1700 | 21,200 | S.T.T.T. | 9 |
| | | 14,000 | 2.42 | 13 |
| | | 11,000 | 8.08 | 13 |
| | | 6,000 | 118.5 | 9 |
| | | 5,000 | 235 | 21 |
| | | 4,000 | 518 | 7 |
| S590 | 1800 | 15,000 | S.T.T.T. | 22 |
| | | 11,000 | 1.42 | 17 |
| | | 8,000 | 8.6 | 22 |
| | | 6,000 | 21 | 18 |
| | | 5,000 | 28 | 17 |
| | | 4,000 | 110 | 16 |
| | | 3,000 | 180 | 52 |
| | | 2,000 | 693 | 10 |
| Inconel-1 | 1700 | (b) | S.T.T.T. | (b) |
| | | 12,000 | 0.20 | 31 |
| | | 4,000 | 45.5 | 19 |
| | | 3,000 | 118 | 27 |
| | | 2,500 | 177.5 | 19 |
| | | 2,250 | 1492 | 96 |
| | | 2,000 | 248 | 36 |
| | | 1,800 | 889 | 57 |
| | | 2,000 | (c) | |
| Inconel-1 | 1800 | (b) | S.T.T.T | ----- |
| | | 4,500 | 5.1 | 19 |
| | | 2,500 | 54 | 28 |
| | | 2,000 | 152.5 | 25 |
| | | 1,500 | 605 | 44 |
| Inconel-2 | 1700 | 4,000 | 30.5 | 22 |
| | | 3,000 | 175 | 60 |
| | | 2,500 | 649 | 49 |
| | | 2,000 | 1103 | 50 |
| | 1800 | 2,500 | 84 | 35 |
| | | 2,250 | 546 | 39 |
| | | 2,000 | 1340 | 54 |

^bNot sufficient material for short-time tensile test.^cOverheated at 382 hr.

TABLE II - Continued

RUPTURE-TEST DATA AT 1700° AND 1800° F - Continued

| Alloy | Temperature (°F) | Stress (psi) | Rupture time (hr) | Elongation (percent) |
|------------------|---------------------|-----------------|----------------------|-------------------------|
| Low-carbon N-155 | 1700 | (b) | S.T.T.T. | ----- |
| | | 10,000 | 21.5 | 12 |
| | | 7,000 | 27 | 23 |
| | | 5,000 | 88 | 11 |
| | | 4,500 | 236 | 16 |
| | | 4,000 | 831 | 7 |
| Low-carbon N-155 | 1800 | (b) | S.T.T.T. | ----- |
| | | 6,000 | 16.5 | 28 |
| | | 5,000 | 17 | 20 |
| | | 4,000 | 81 | 21 |
| | | 3,000 | 176.5 | 22 |
| | | 2,500 | 340 | 20 |
| J-837 | 1700 | 20,400 | S.T.T.T. | 58 |
| | | 6,000 | 33 | (d) |
| | | 5,000 | 31 | (d) |
| J-837 | 1800 | 12,600 | S.T.T.T. | 47 |
| | | 4,000 | 9 | (d) |
| J-838 | 1700 | 20,700 | S.T.T.T. | 67 |
| | | 17,000 | 1.42 | 54 |
| | | 13,000 | 8.5 | 57 |
| | | 9,000 | 33 | 54 |
| | | 7,000 | 132 | 66 |
| | | 6,000 | 284.5 | 42 |
| | | 5,000 | 434 | 35 |
| | | | | |
| J-838 | 1800 | 12,900 | S.T.T.T. | 53 |
| | | 10,000 | 2.00 | 39 |
| | | 5,000 | 34.5 | 29 |
| | | 4,000 | 117 | 61 |
| | | 3,000 | 186 | 40 |
| | | 2,500 | 313.5 | 37 |
| | | | | |
| J-839 | 1700 | 23,300 | S.T.T.T. | 62 |
| | | 6,000 | 33 | (d) |
| J-839 | 1800 | 13,200 | S.T.T.T. | 33 |


^bNot sufficient material for short-time tensile test.^dSpecimen severely oxidized.

TABLE II - Continued

RUPTURE-TEST DATA AT 1700° AND 1800° F - Continued

| Alloy | Temperature (°F) | Stress (psi) | Rupture time (hr) | Elongation (percent) |
|-------------------|---------------------|-----------------|----------------------|-------------------------|
| J-840 | 1700 | 19,200 | S.T.T.T. | 73 |
| | | 14,000 | 2.67 | 51 |
| | | 7,000 | 46 | 25 |
| | | 6,000 | 160 | 26 |
| | | 5,000 | 144 | 16 |
| | | 4,000 | 214 | 27 |
| | | 3,000 | 1133 | 15 |
| | | | | |
| J-840 | 1800 | 14,000 | S.T.T.T. | 66 |
| | | 9,000 | 2.67 | 40 |
| | | 4,000 | 24.5 | 34 |
| | | 3,000 | 52 | 19 |
| | | 2,500 | 232 | 22 |
| | | 2,000 | 233 | 36 |
| | | 1,700 | 1309 | 28 |
| | | | | |
| Type 330 | 1700 | 9,740 | S.T.T.T. | 44 |
| | | 7,000 | 2.17 | 56 |
| | | 4,000 | 17 | 28 |
| | | 2,700 | 46.5 | 36 |
| | | 2,000 | 88 | 25 |
| | | 2,000 | 147 | 34 |
| | | 1,750 | 153 | 43 |
| | | 1,650 | 233 | 33 |
| | | 1,500 | 811 | 60 |
| | | 1,500 | 525 | 60 |
| Type 310 | 1700 | 13,700 | S.T.T.T. | 18 |
| | | 9,000 | 2.0 | 20 |
| | | 4,000 | 85 | 20 |
| | | 3,000 | 285.5 | 15 |
| | | 2,500 | 728 | 10 |
| | | | | |
| Type 310 | 1800 | 9,650 | S.T.T.T. | 25 |
| Type 310S (AF-18) | 1700 | 15,600 | S.T.T.T. | 42 |
| | | 11,000 | 1.05 | 12 |
| | | 9,000 | 5.00 | 5 |
| | | 5,000 | 87 | 7 |
| | | 4,000 | 276 | 6 |
| | | 3,000 | 1124 | 3.5 |

TABLE II - Concluded

RUPTURE-TEST DATA AT 1700° AND 1800° F - Concluded

| Alloy | Temperature (°F) | Stress (psi) | Rupture time (hr) | Elongation (percent) |
|-------------------|---------------------|-----------------|----------------------------------|-------------------------|
| Type 310S (AF-18) | 1800 | 12,900 | S.T.T.T. | 26 |
| | | 8,000 | 2.0 | 14 |
| | | 6,500 | 11.2 | 16 |
| | | 4,000 | 75.0 | 7 |
| | | 3,500 | 112 | 5 |
| | | 3,000 | 231 | 5 |
| | | 2,500 | 289 | 6 |
| | | 2,200 | 384 | 4 |
| Type 310S (14626) | 1700 | 10,200 | S.T.T.T. | 43 |
| | | 5,000 | 25 | 6 |
| | | 4,000 | 64 | 10 |
| | | 3,000 | 233 | 9 |
| | | 2,400 | 397 | 7 |
| Type 310S (14626) | 1800 | 7,550 | S.T.T.T. | 33 |
| | | 4,000 | 23 | 54 |
| | | 3,000 | 85 | 8 |
| | | 2,000 | 345 | 4 |
| | | 1,700 | 569 | 5 |
| Type 309 | 1700 | 10,390 | S.T.T.T. | 51 |
| | | 7,000 | 2.87 | 45 |
| | | 4,000 | 36 | 27 |
| | | 3,000 | 109 | 21 |
| | | 2,500 | 277 | 7 |
| Type 309 | 1800 | 6,810 | S.T.T.T. | 51 |
| | | 4,500 | 7.5 | 15 |
| | | 2,500 | 95.5 | 15 |
| | | 2,300 | 254 | 14 |
| | | 2,000 | 93.5 | 18 |
| | | 1,800 | 321 | 10 |
| | | 1,500 | Discontinued after 1772 hr | 8 |

TABLE III

RUPTURE STRENGTHS OF SHEET ALLOYS AT 1700° AND 1800° F

[From curves of stress against rupture time, fig. 1]

| Alloy | Temperature (°F) | Stress for rupture in indicated time periods (psi) | | | | |
|-------------------|---------------------|---|--------|--------|--------|-------------------|
| | | 1 hr | 10 hr | 100 hr | 400 hr | 1000 hr |
| Vitallium | 1700 | 18,500 | 12,000 | 8000 | 4600 | 3300 |
| Co-Cr-Ni | 1700 | 14,000 | 10,500 | 5600 | 3700 | ^a 2800 |
| S816 | 1700 | 18,000 | 10,500 | 4500 | 2700 | 1900 |
| S590 | 1700 | 17,000 | 10,500 | 6300 | 4300 | 3400 |
| Inconel-1 | 1700 | 10,000 | 5,600 | 3100 | 2200 | 1750 |
| Inconel-2 | 1700 | ----- | 4,800 | 3300 | 2700 | 2100 |
| Low-carbon N-155 | 1700 | ----- | ----- | 5300 | 4400 | 3900 |
| J-837 | 1700 | (b) | (b) | (b) | (b) | (b) |
| J-838 | 1700 | 19,000 | 12,000 | 7400 | 5200 | ^a 3500 |
| J-839 | 1700 | (b) | (b) | (b) | (b) | (b) |
| J-840 | 1700 | 18,000 | 10,000 | 5600 | 3900 | 3100 |
| Type 330 | 1700 | 8,500 | 4,600 | 1950 | 1600 | 1400 |
| Type 310 | 1700 | 10,500 | 6,400 | 3800 | 2850 | 2300 |
| Type 310S (AF-18) | 1700 | 11,000 | 8,000 | 5000 | 3700 | 3100 |
| Type 310S (14626) | 1700 | ----- | 6,400 | 3600 | 2500 | ^a 2000 |
| Type 309 | 1700 | 8,800 | 5,200 | 3100 | 2300 | ^a 1900 |
| Vitallium | 1800 | 13,500 | 7,800 | 4200 | 2500 | ^a 1800 |
| Co-Cr-Ni | 1800 | 11,500 | 8,600 | 4000 | 2300 | ^a 1600 |
| S816 | 1800 | 11,200 | 5,600 | 2200 | 1270 | ^a 800 |
| S590 | 1800 | 11,800 | 7,600 | 3700 | 2400 | 1800 |
| Inconel-1 | 1800 | ^a 6,500 | 3,800 | 2200 | 1600 | 1300 |
| Inconel-2 | 1800 | ----- | ----- | 2500 | 2200 | 2000 |
| Low-carbon N-155 | 1800 | ----- | 6,800 | 3500 | 2400 | ^a 1850 |
| J-838 | 1800 | 11,000 | 6,800 | 4100 | 2300 | ^a 1500 |
| J-840 | 1800 | 13,000 | 5,500 | 2700 | 2100 | 1800 |
| Type 310S (AF-18) | 1800 | 9,000 | 6,600 | 3600 | 2200 | ^a 1600 |
| Type 310S (14626) | 1800 | ----- | 4,800 | 2900 | 1900 | 1400 |
| Type 309 | 1800 | ^a 7,000 | 4,100 | 2450 | 1800 | 1500 |

NACA

^aObtained by extrapolation.^bLow because of severe oxidation.

TABLE IV

ESTIMATED RUPTURE ELONGATIONS OF SHEET ALLOYS AT 1700° AND 1800° F


| Alloy | Temperature (°F) | Estimated elongation to fracture in indicated time periods (percent) | | | | |
|-------------------|---------------------|--|-------|--------|--------|---------|
| | | 1 hr | 10 hr | 100 hr | 400 hr | 1000 hr |
| Vitallium | 1700 | 15 | 15 | 14 | 15 | 20 |
| Co-Cr-Ni | 1700 | 4 | 9 | 2 | 3 | -- |
| S816 | 1700 | 15 | 20 | 20 | 20 | 40 |
| S590 | 1700 | 13 | 13 | 9 | 15 | 7 |
| Inconel-1 | 1700 | 30 | 25 | 25 | 40 | 55 |
| Inconel-2 | 1700 | -- | 20 | 40 | 55 | 50 |
| Low-carbon N-155 | 1700 | -- | 12 | 11 | 15 | 7 |
| J-838 | 1700 | 60 | 57 | 60 | 40 | -- |
| J-840 | 1700 | 55 | 50 | 25 | 20 | 15 |
| Type 330 | 1700 | 55 | 30 | 25 | 40 | 60 |
| Type 310 | 1700 | 20 | 20 | 20 | 15 | 10 |
| Type 310S (AF-18) | 1700 | 12 | 5 | 7 | 6 | 4 |
| Type 310S (14626) | 1700 | -- | 6 | 10 | 7 | -- |
| Type 309 | 1700 | 50 | 40 | 21 | 7 | -- |
| Vitallium | 1800 | 20 | 15 | 15 | 12 | -- |
| Co-Cr-Ni | 1800 | 10 | 10 | 4 | 2 | -- |
| S816 | 1800 | 30 | 30 | 35 | 45 | -- |
| S590 | 1800 | 17 | 22 | 16 | 30 | 10 |
| Inconel-1 | 1800 | -- | 19 | 26 | 30 | 45 |
| Inconel-2 | 1800 | -- | -- | 35 | 40 | 50 |
| Low-carbon N-155 | 1800 | -- | 28 | 21 | 20 | -- |
| J-838 | 1800 | 45 | 30 | 60 | 37 | -- |
| J-840 | 1800 | 45 | 40 | 20 | 25 | 28 |
| Type 310S (AF-18) | 1800 | 15 | 15 | 6 | 4 | -- |
| Type 310S (14626) | 1800 | -- | 55 | 8 | 4 | -- |
| Type 309 | 1800 | 50 | 15 | 15 | 10 | -- |

TABLE V
COMPARATIVE 1700° AND 1800° F RUPTURE PROPERTIES OF SEVEN ALLOYS
IN THE FORM OF SHEET, BAR STOCK, AND PRECISION CASTINGS

| Alloy | Temperature (°F) | Form | Treatment (a) | Rupture strength (psi) | | Estimated rupture ductility (percent) | | Source of data, reference |
|------------------|---------------------|-----------|----------------------------------|---------------------------|--------------------|--|---------|---------------------------------|
| | | | | 100 hr | 1000 hr | 100 hr | 1000 hr | |
| Vitallium | 1700 | Sheet | Annealed | 8,000 | 3,300 | 14 | 20 | 1 |
| Vitallium | 1700 | Cast | ----- | 13,000 | 10,000 | 8 | 5 | |
| Vitallium | 1800 | Sheet | Annealed | 4,200 | ^b 1,800 | 15 | ----- | 1 |
| Vitallium | 1800 | Cast | ----- | 9,400 | 7,000 | 13 | 12 | |
| S816 | 1700 | Sheet | A.C.2200-2250° F | 4,500 | 1,900 | 20 | 40 | 1 |
| S816 | 1700 | Bar stock | W.Q.2300° F+ 16 hr at 1700° F | 9,500 | 6,100 | 15 | 15 | |
| S816 | 1700 | Cast | ----- | 14,500 | 11,500 | 10 | 6 | 1 |
| S816 | 1800 | Sheet | A.C.2200-2250° F | 2,200 | ^b 800 | 35 | ----- | 1 |
| S816 | 1800 | Bar stock | W.Q.2300° F+ 16 hr at 1800° F | 5,300 | 3,000 | 10 | ----- | |
| S816 | 1800 | Cast | ----- | 10,500 | 7,800 | 10 | ----- | 1 |
| S590 | 1700 | Sheet | A.C.2150° F | 6,300 | 3,400 | 9 | 7 | 1 |
| S590 | 1700 | Bar stock | W.Q.2270° F+ 16 hr at 1700° F | 9,400 | 6,600 | 30 | 14 | 1 |
| S590 | 1700 | Cast | ----- | 11,000 | 8,400 | 15 | 8 | 1 |
| S590 | 1800 | Sheet | A.C.2150° F | 3,700 | 1,800 | 16 | 10 | 1 |
| S590 | 1800 | Bar stock | W.Q.2270° F+ 16 hr at 1800° F | 5,600 | 3,500 | 25 | ----- | |
| S590 | 1800 | Cast | ----- | 8,000 | 5,800 | 15 | 5 | 1 |
| Low-carbon N-155 | 1700 | Sheet | A.C.2000-2100° F | 5,300 | 3,900 | 11 | 7 | 1 |
| Low-carbon N-155 | 1700 | Bar stock | Hot-rolled | 5,100 | 2,500 | 30 | ----- | |
| Low-carbon N-155 | 1700 | Bar stock | A.C.2282° F | 7,600 | 4,800 | 20 | 10 | 1 |
| Low-carbon N-155 | 1800 | Sheet | A.C.2000-2100° F | 3,500 | ^b 1,850 | 21 | ----- | 1 |
| Low-carbon N-155 | 1800 | Bar stock | A.C.2282° F | 4,900 | 2,800 | 11 | ----- | |
| 25-12 (309) | 1700 | Sheet | Annealed | 3,100 | ^b 1,900 | 21 | ----- | 2 |
| 25-12 | 1700 | Bar stock | W.Q.2200° F | 4,000 | 2,100 | | | |
| 25-12 | 1700 | Bar stock | W.Q.1900° F | 2,700 | 1,300 | | | |
| 25-12 (309) | 1800 | Sheet | Annealed | 2,450 | 1,500 | 15 | ----- | 2 |
| 25-12 | 1800 | Bar stock | W.Q.2200° F | 2,200 | 1,050 | | | |
| 25-12 | 1800 | Bar stock | W.Q.1900° F | 1,800 | 1,000 | | | |
| 35-15 (330) | 1700 | Sheet | A.C.1950° F | 1,950 | 1,400 | 25 | 60 | 2 |
| 35-15 | 1700 | Bar stock | W.Q.2000° F | 3,000 | 1,800 | | | |
| 35-15 | 1800 | Bar stock | W.Q.2000° F | 2,000 | 1,200 | | | 2 |
| 25-20 (310) | 1700 | Sheet | A.C.2050° F | 3,800 | 2,300 | 20 | 10 | 2 |
| 25-20 | 1700 | Bar stock | W.Q.2150° F | 4,200 | 3,500 | | | |
| 25-20 | 1700 | Bar stock | N. 1700° F | 1,800 | 1,400 | | | 2 |
| 25-20 (310) | 1800 | Bar stock | W.Q.2150° F | 2,750 | 1,900 | | | 2 |
| 25-20 | 1800 | Bar stock | N. 1700° F | 1,500 | 820 | | | 2 |

^aA.C. - air-cooled; W.Q. - water-quenched; N. - normalized.

^bObtained by extrapolation.








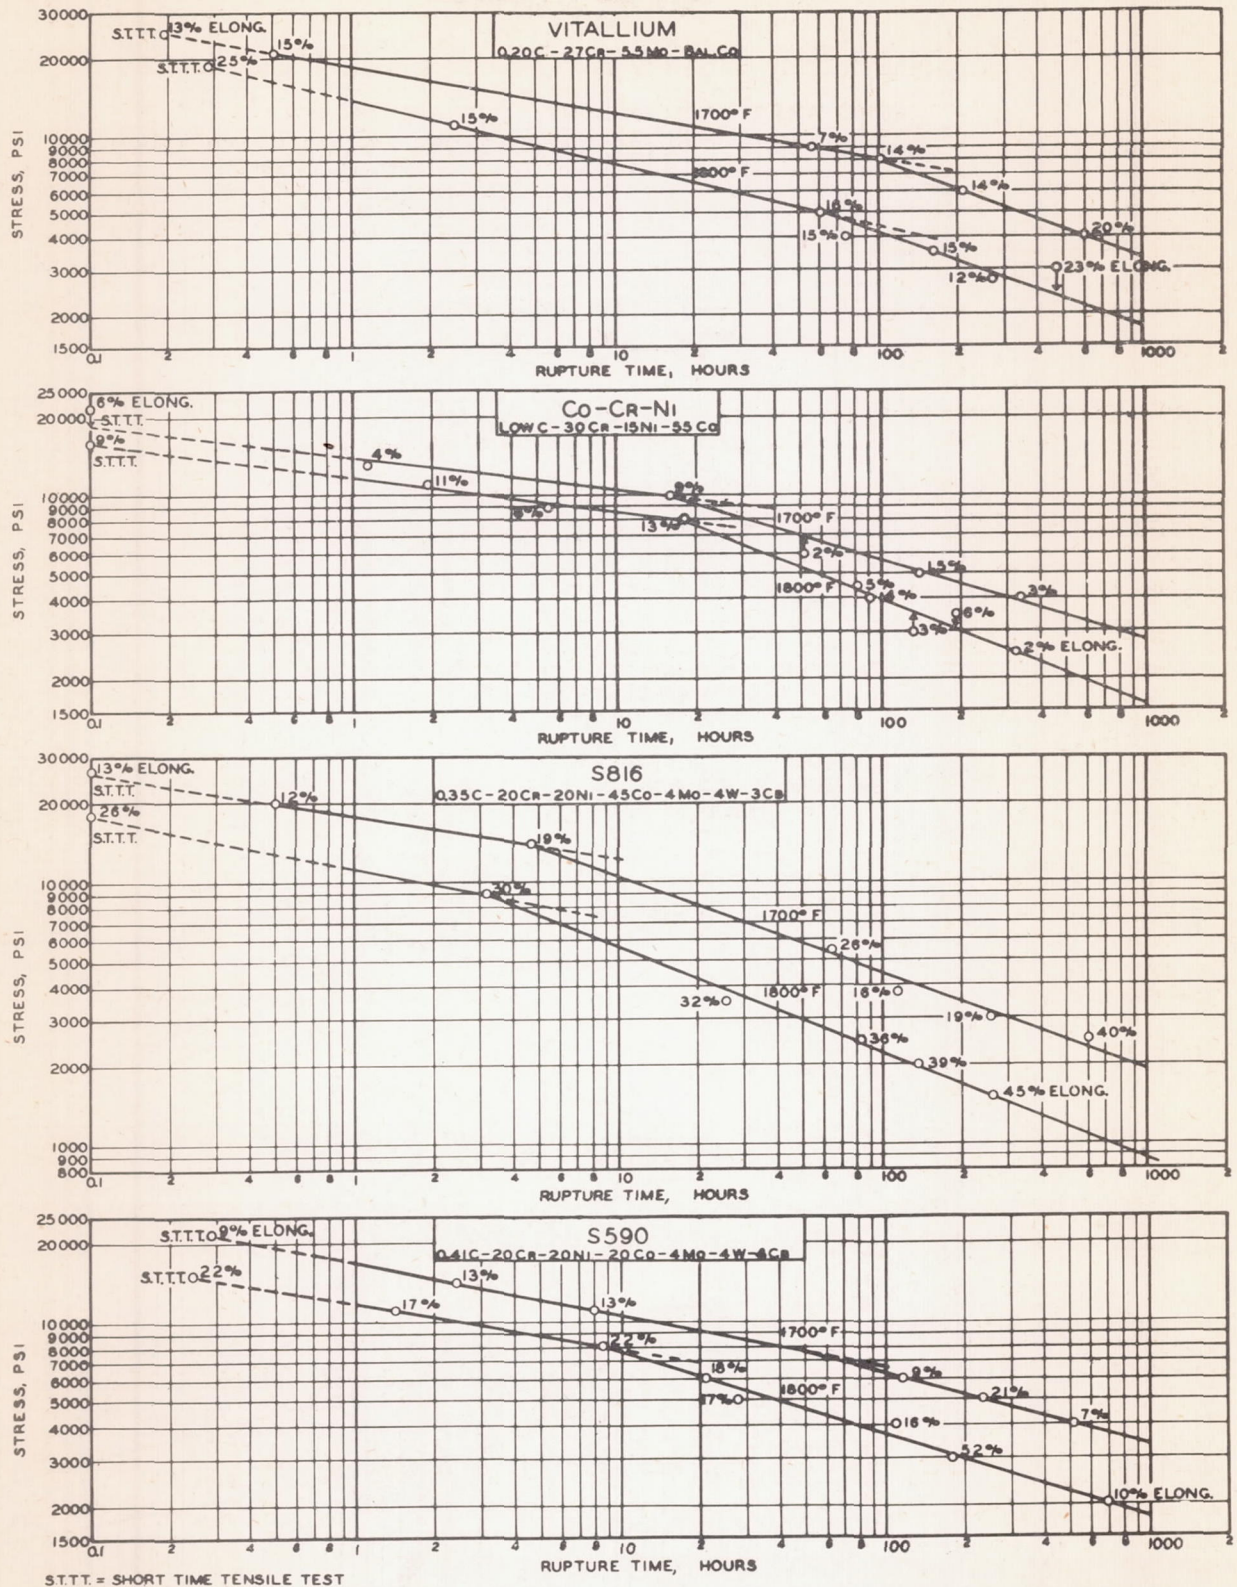


Figure 1.- Stress-rupture-time curves at 1700° and 1800° F for sheet alloys.

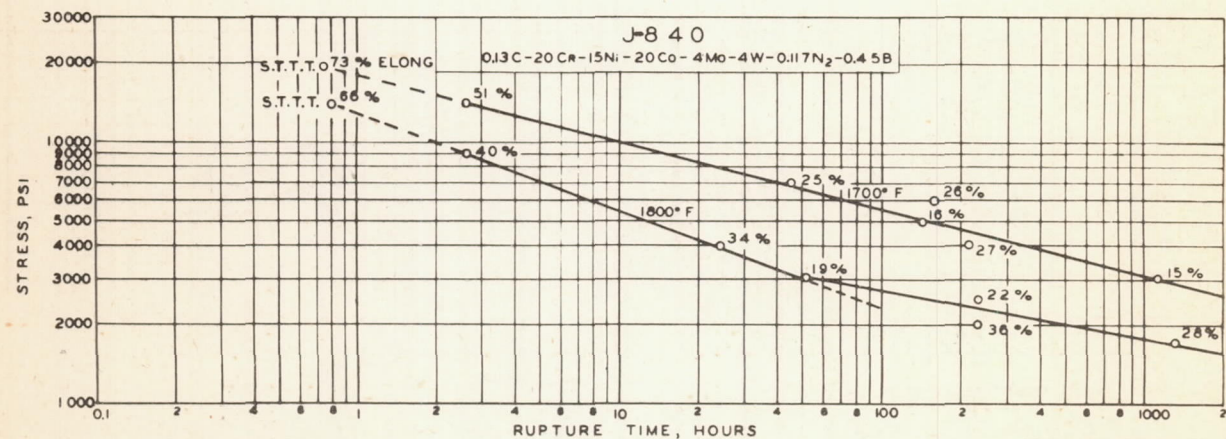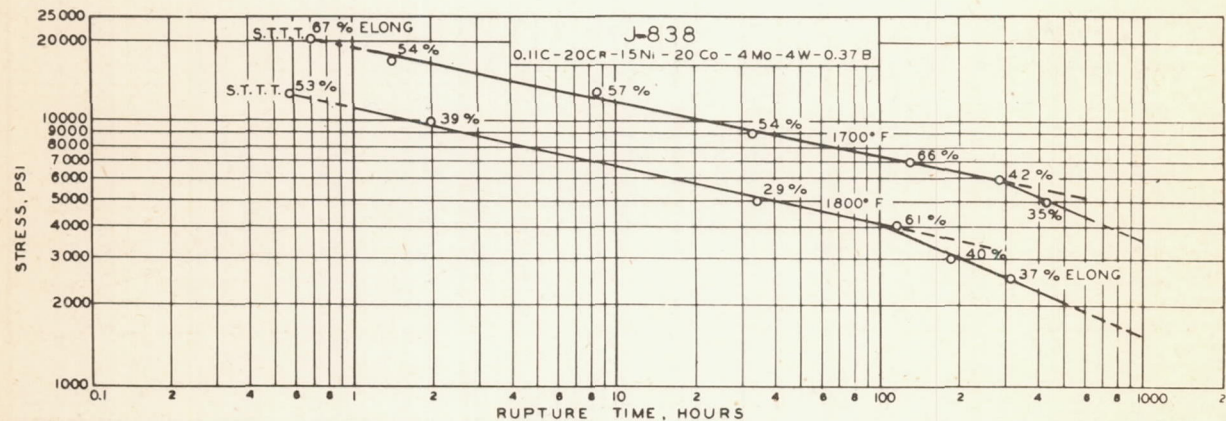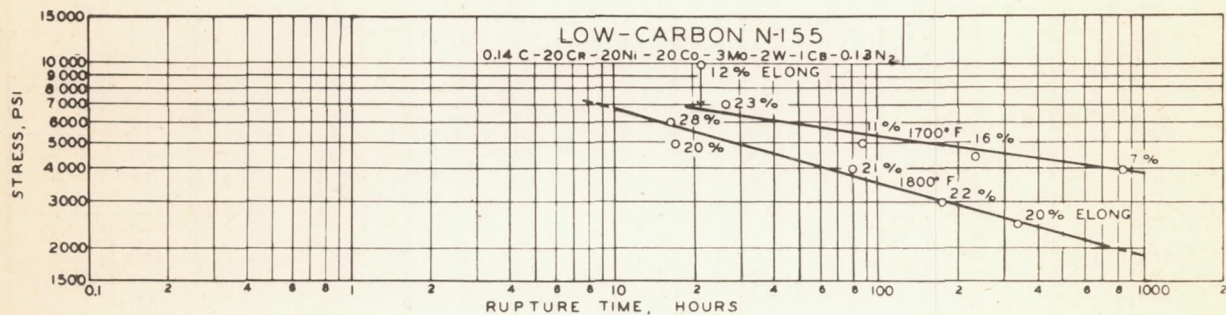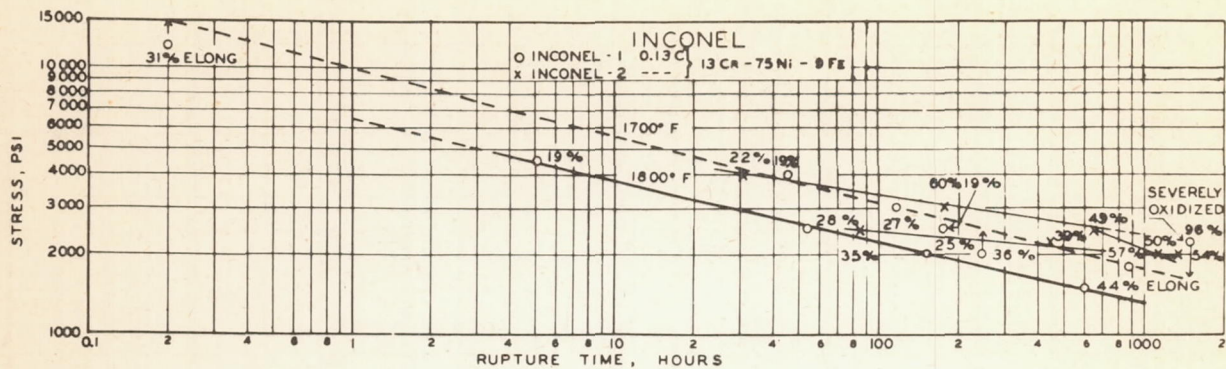

S.T.T.T. = SHORT TIME TENSILE TEST

Figure 1.- Continued.



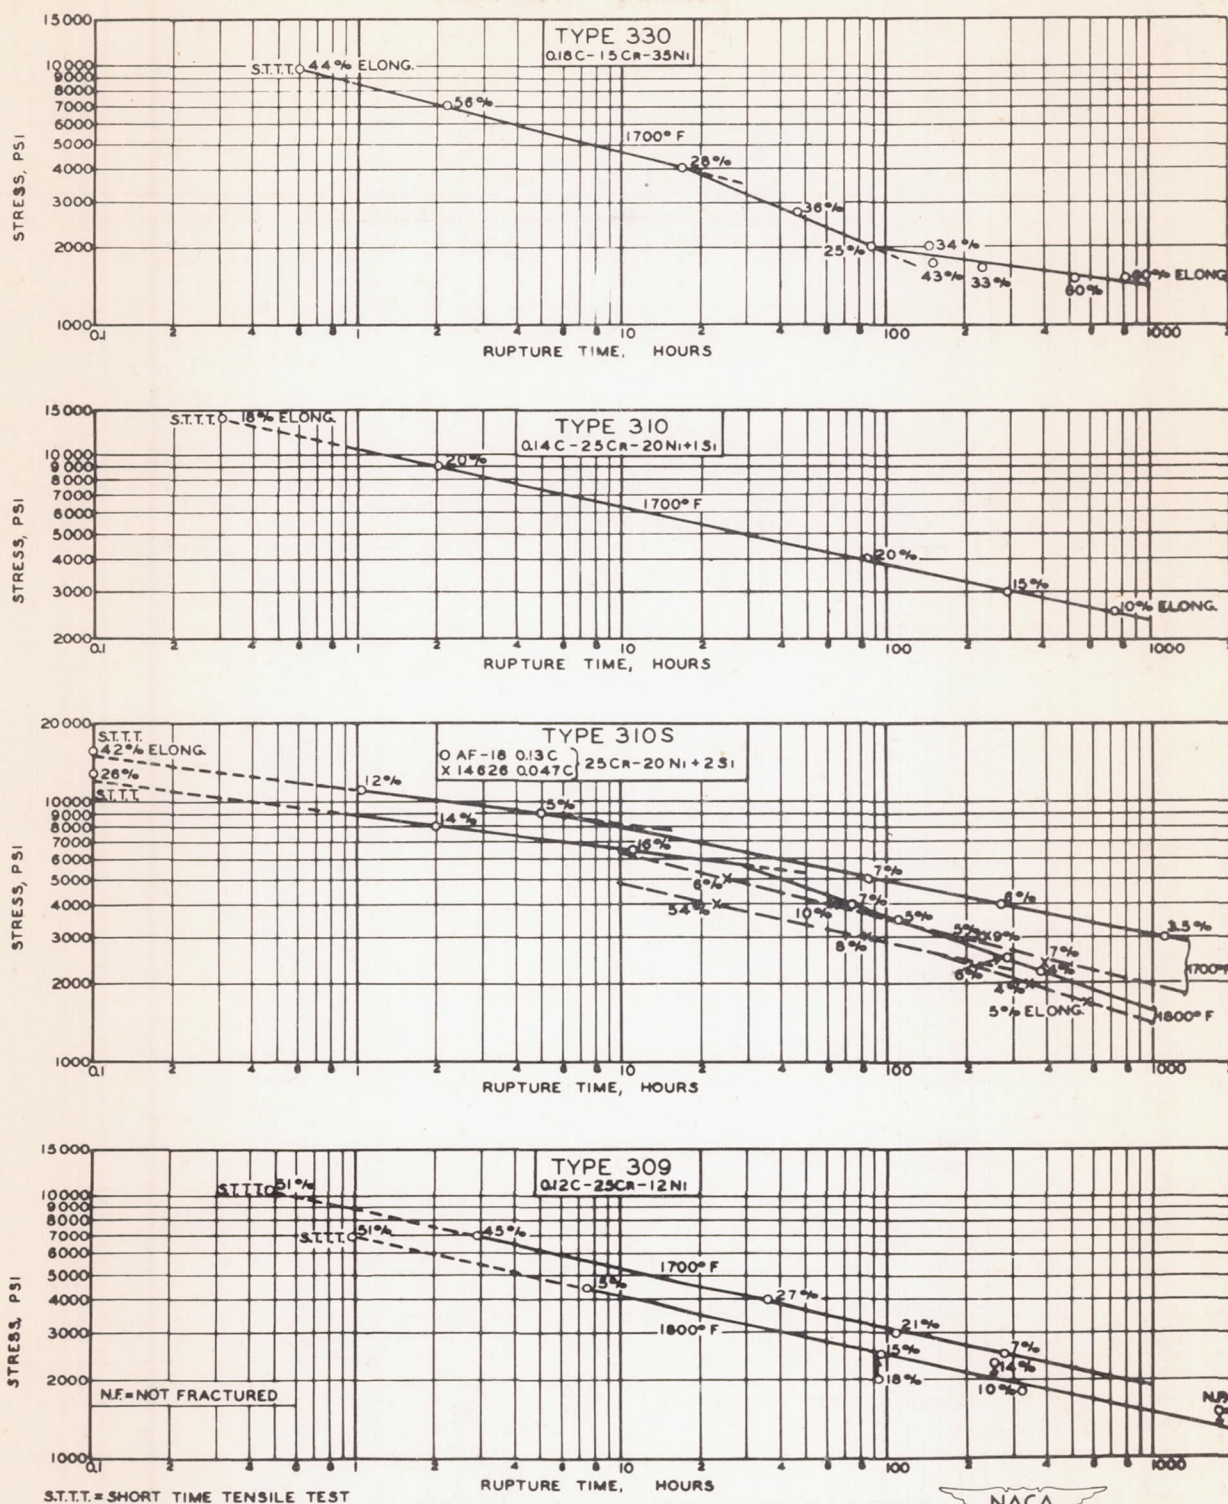


Figure 1.- Concluded


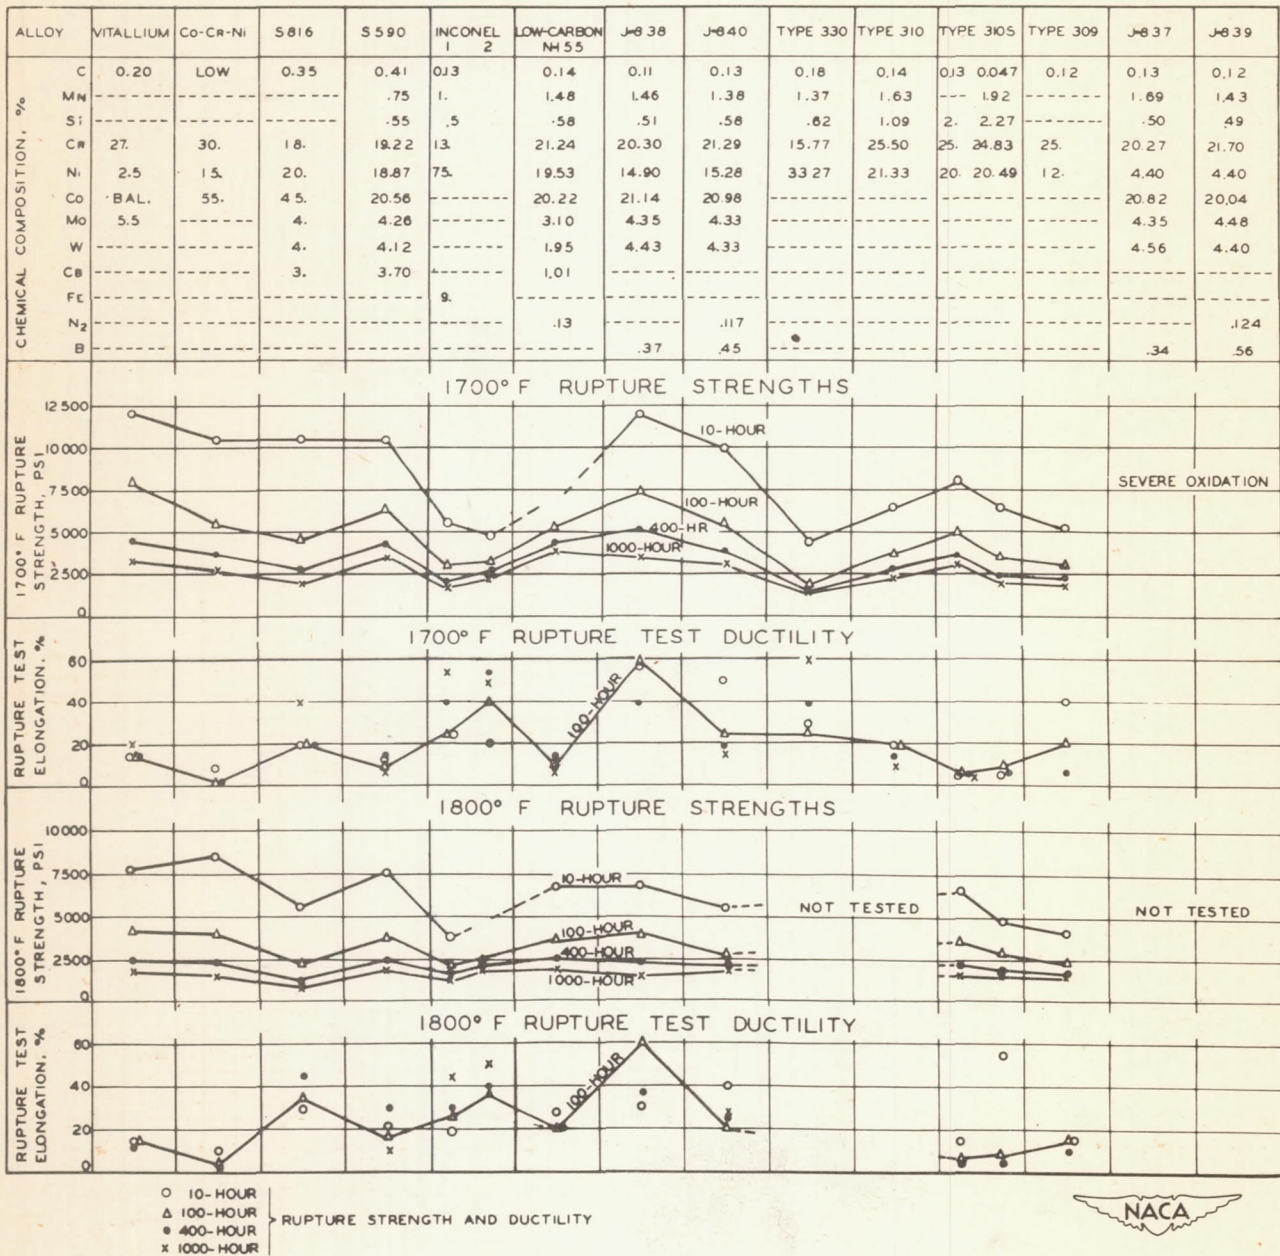




Figure 2.- Comparative rupture properties at 1700° and 1800° F for sheet alloys.

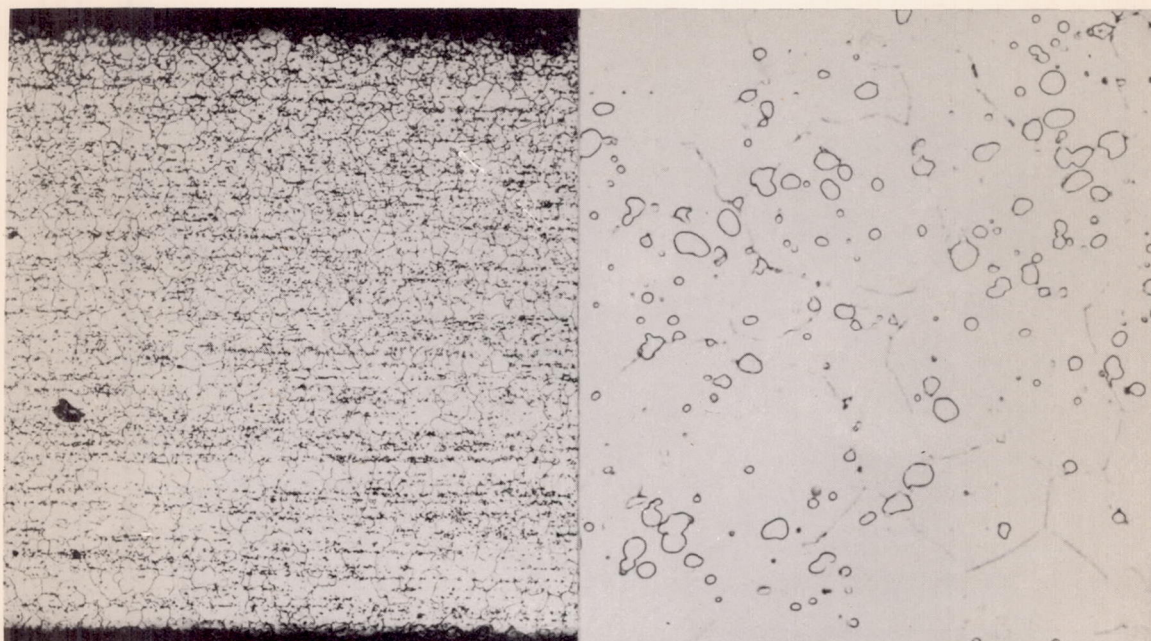

100X

1000X

(a) Original microstructure.

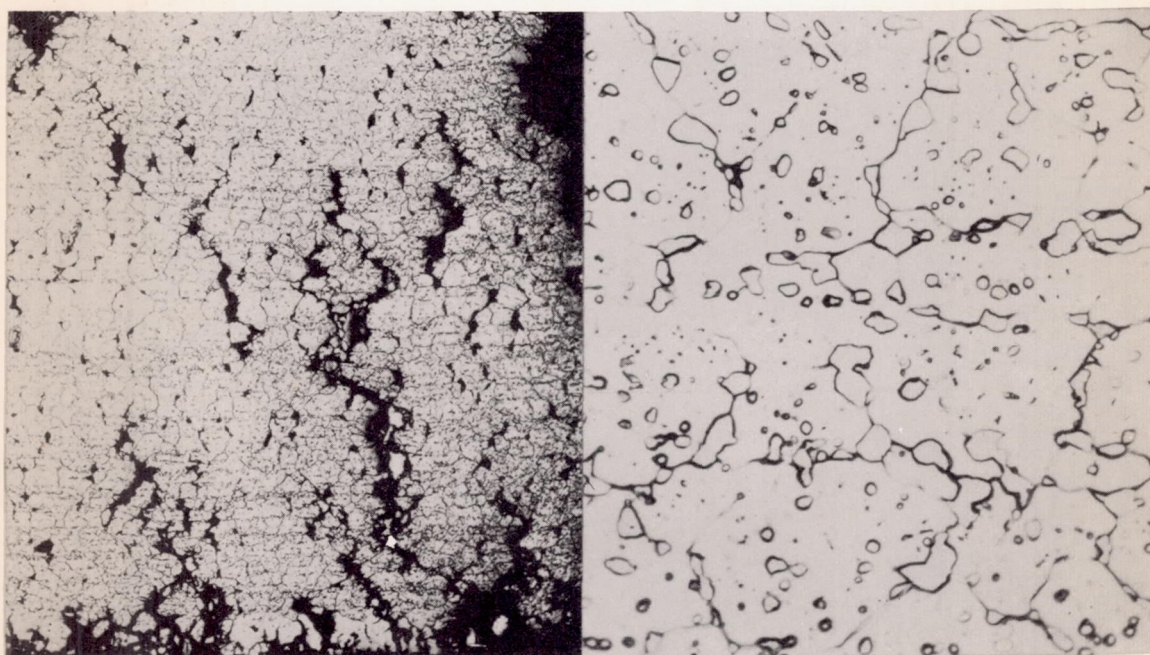

Fracture - 100X

Interior - 1000X

(b) 599 hours for rupture at 1700° F under 4000 psi.


Figure 3.- Microstructure of sheet Vitallium alloy. Electrolytic chromic acid etch.

Figure 1 - Minimum and maximum values of the

Figure 2 - Minimum and maximum values of the

Figure 3 - Minimum and maximum values of the

Figure 4 - Minimum and maximum values of the


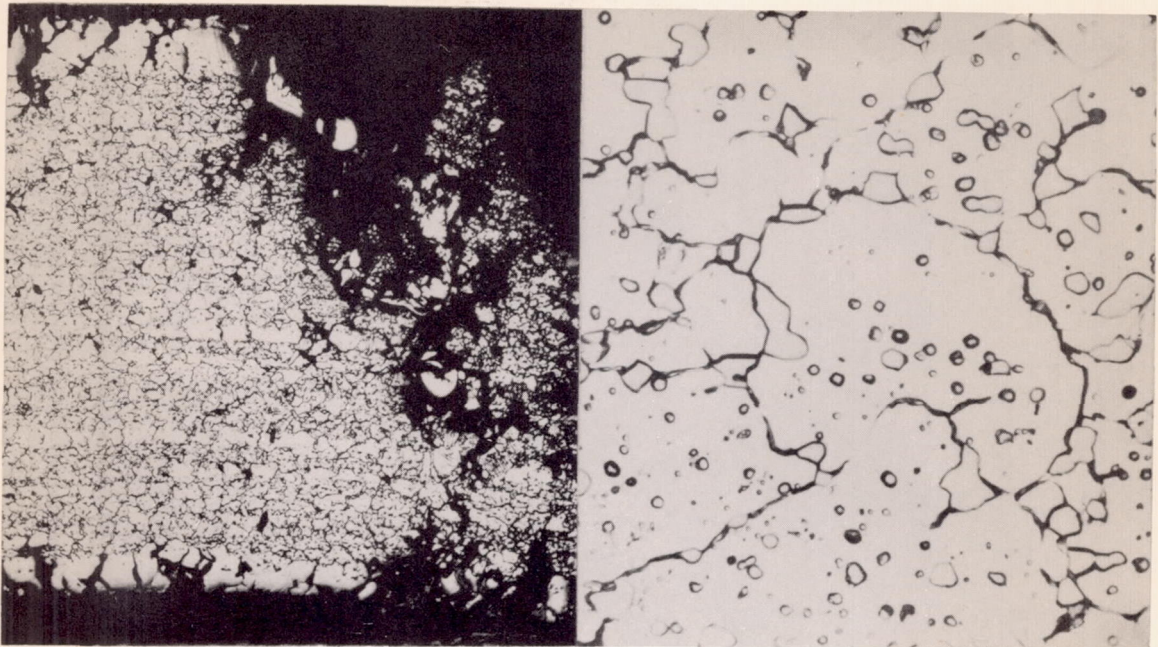


Fracture - 100X

Interior - 1000X

(c) 472 hours for rupture at 1800° F under 3000 psi.

Figure 3.- Concluded.

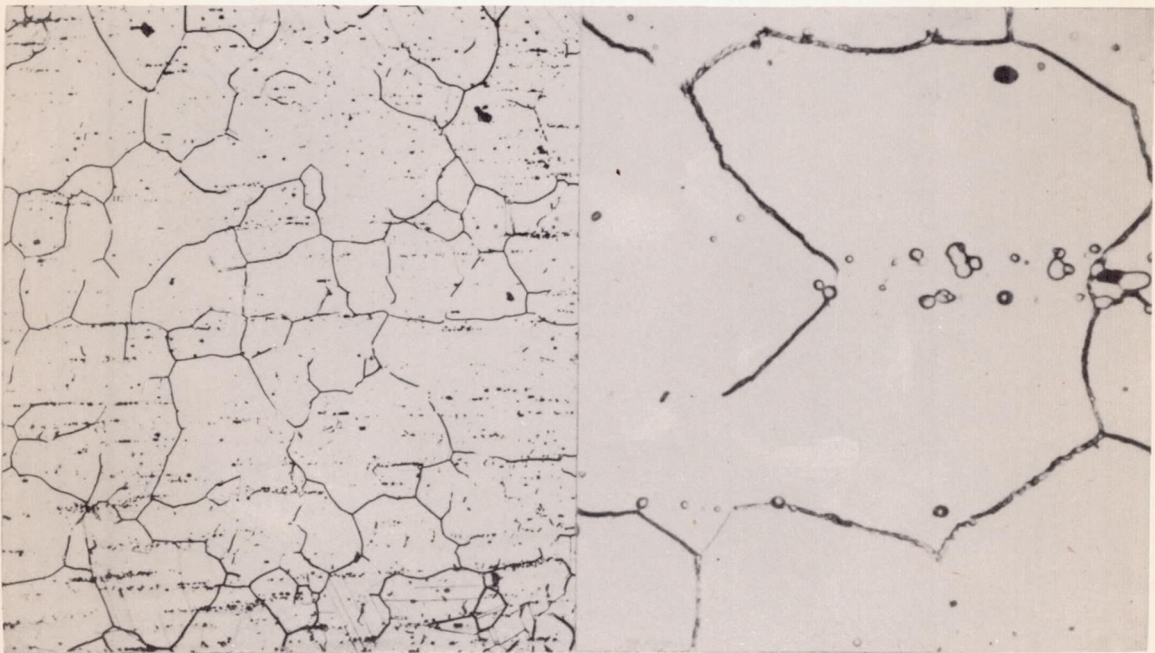


100X

1000X


(a) Original microstructure.

Figure 4.- Microstructures of sheet Co-Cr-Ni alloy. Electrolytic chromic acid etch.

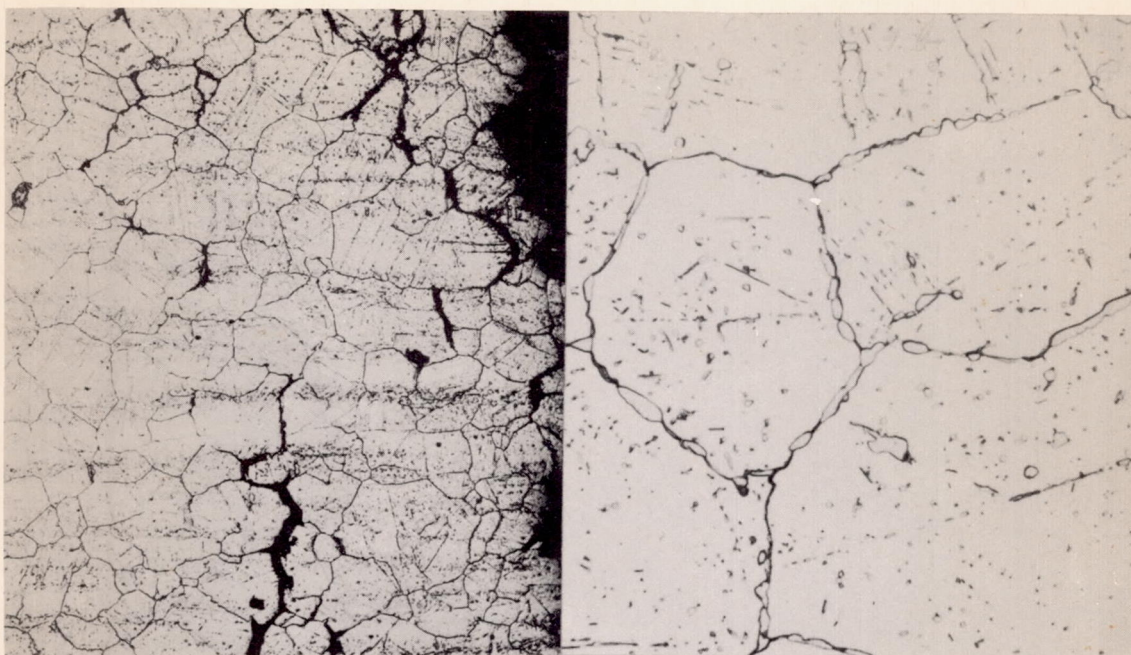


Fracture - 100X

Interior - 1000X



(b) 333.5 hours for rupture at 1700° F under 4000 psi.

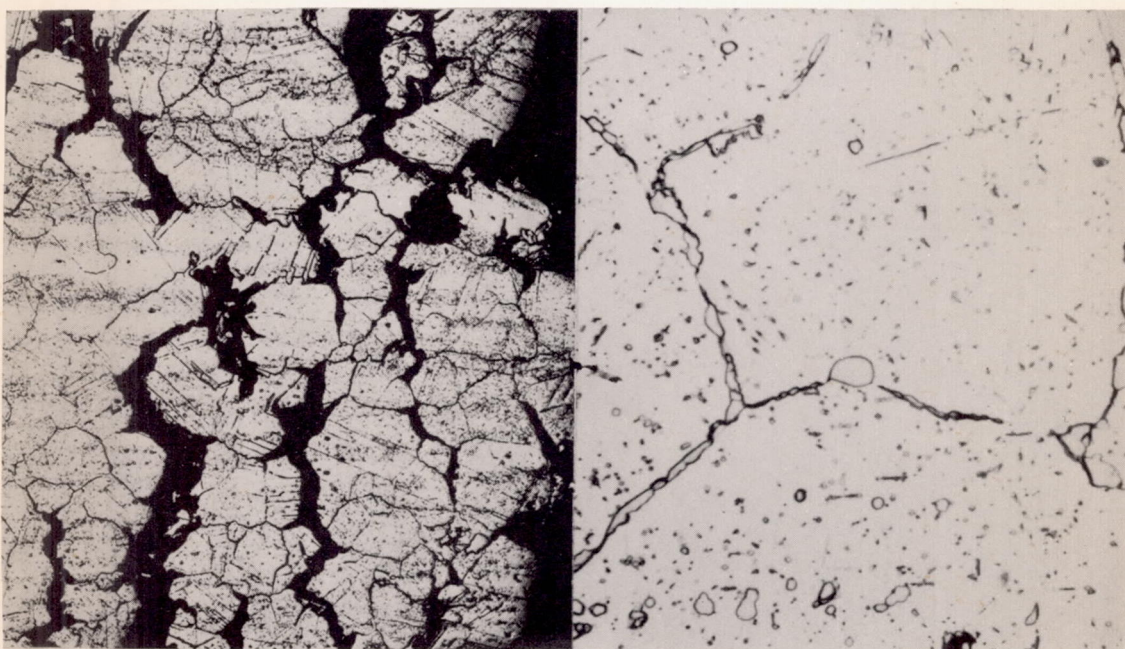


Fracture - 100X

Interior - 1000X

(c) 324 hours for rupture at 1800° F under 2500 psi.



Figure 4.- Concluded

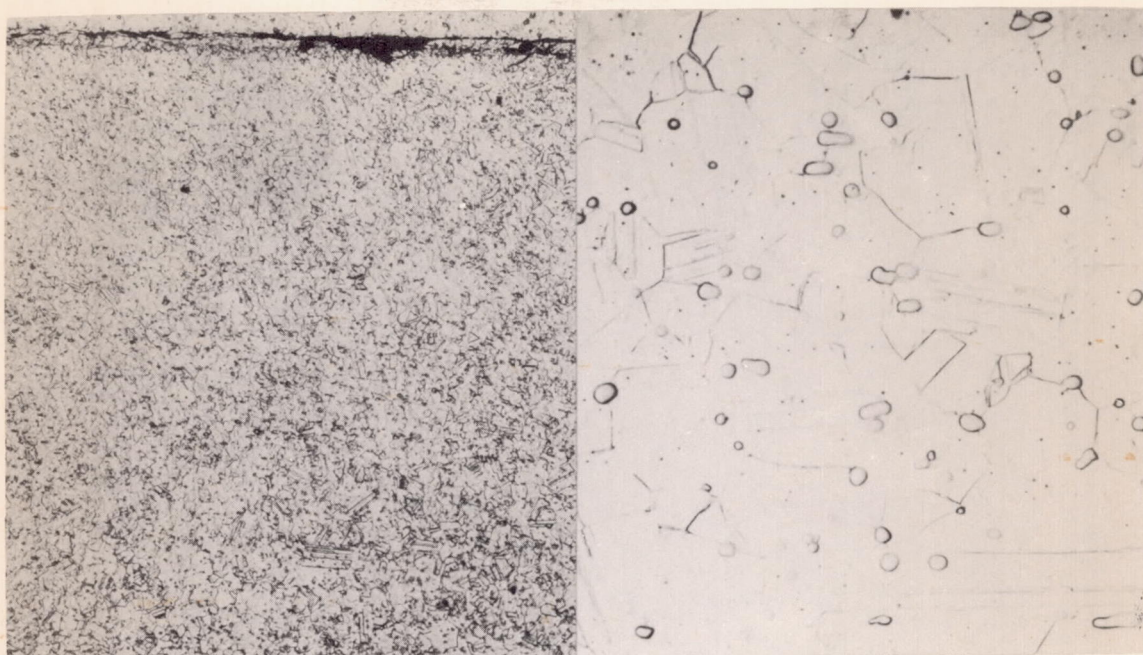

100X

1000X

(a) Original microstructure.

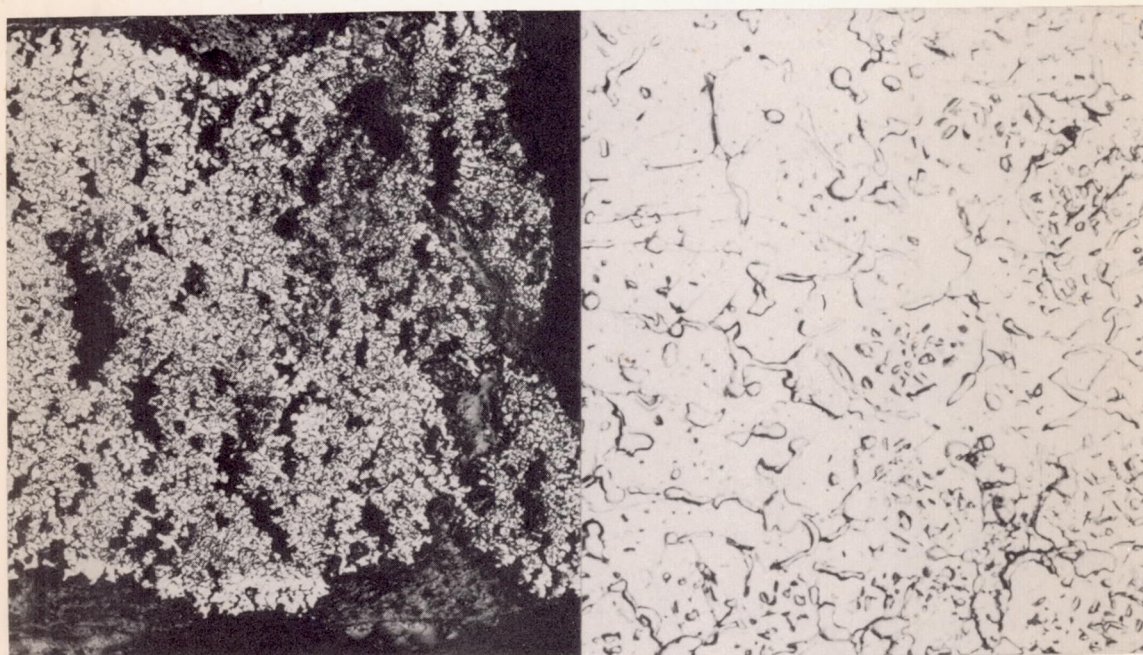


Fracture - 100X

Interior - 1000X

(b) 600 hours for rupture at 1700° F under 2500 psi.

Figure 5.- Microstructures of sheet S816 alloy. Acid ferric chloride etch.


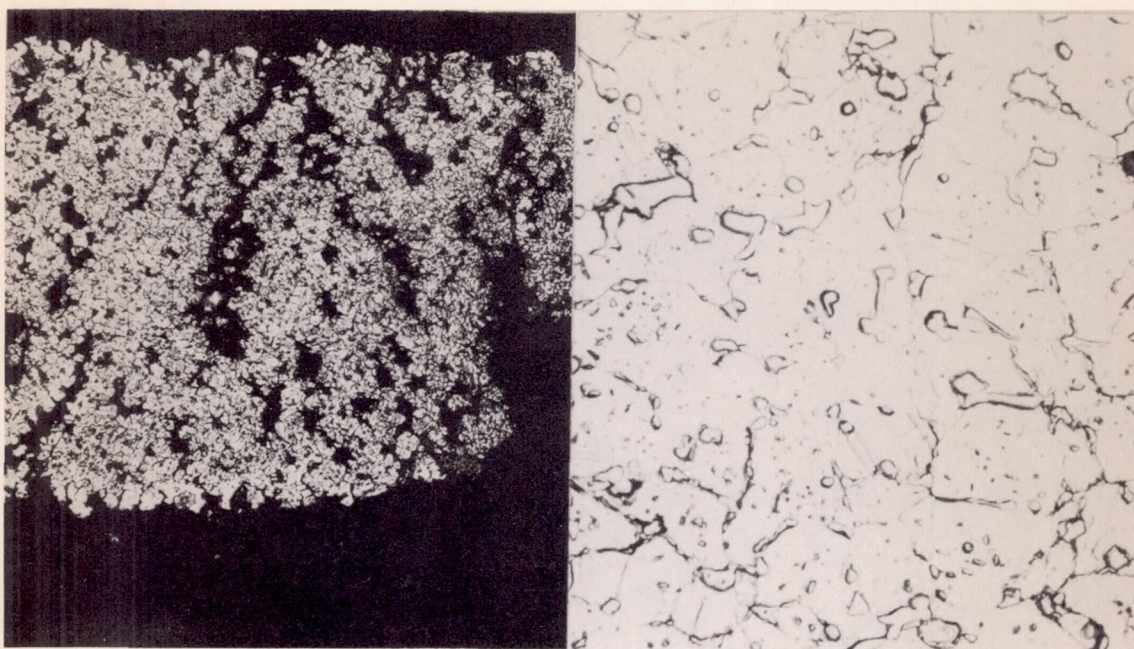


Fracture - 100X

Interior - 1000X

(c) 259.5 hours for rupture at 1800° F under 1500 psi.

Figure 5.- Concluded.

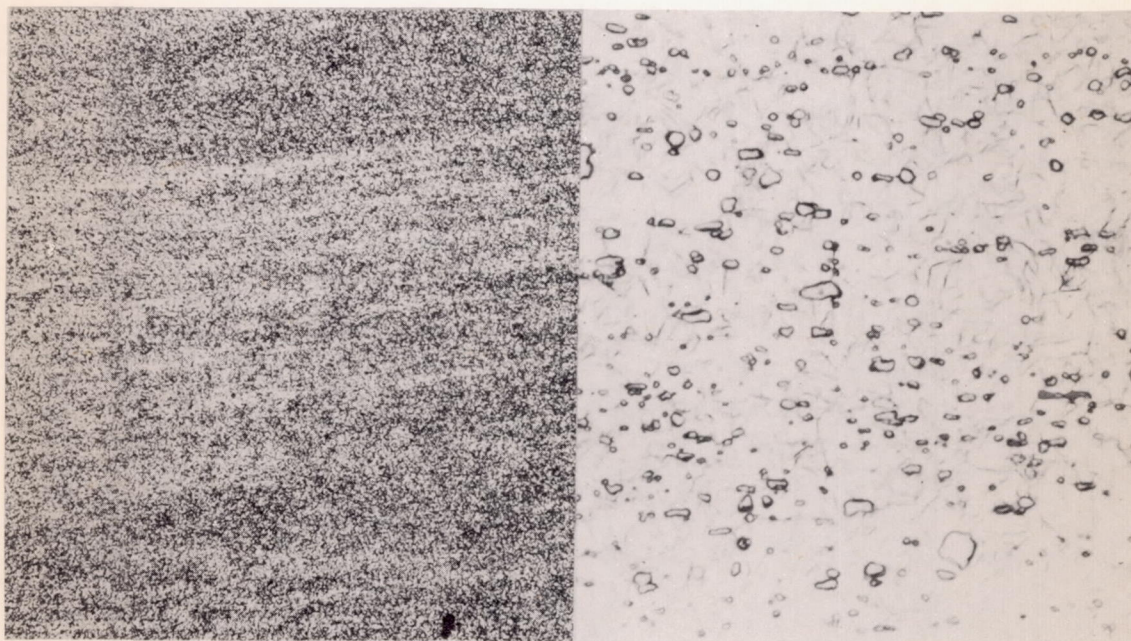

100X

1000X

(a) Original microstructure.

Figure 6.- Microstructures of sheet S590 alloy. Acid ferric chloride etch.


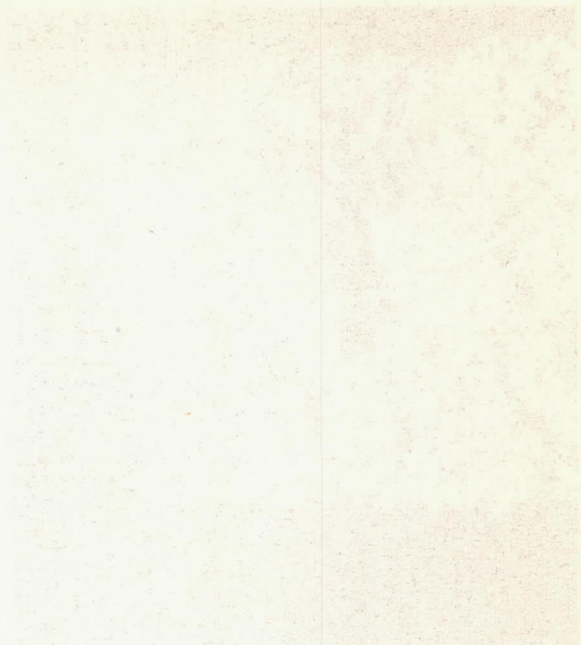


Figure 1 - (c) 1950




Figure 2 - (c) 1950

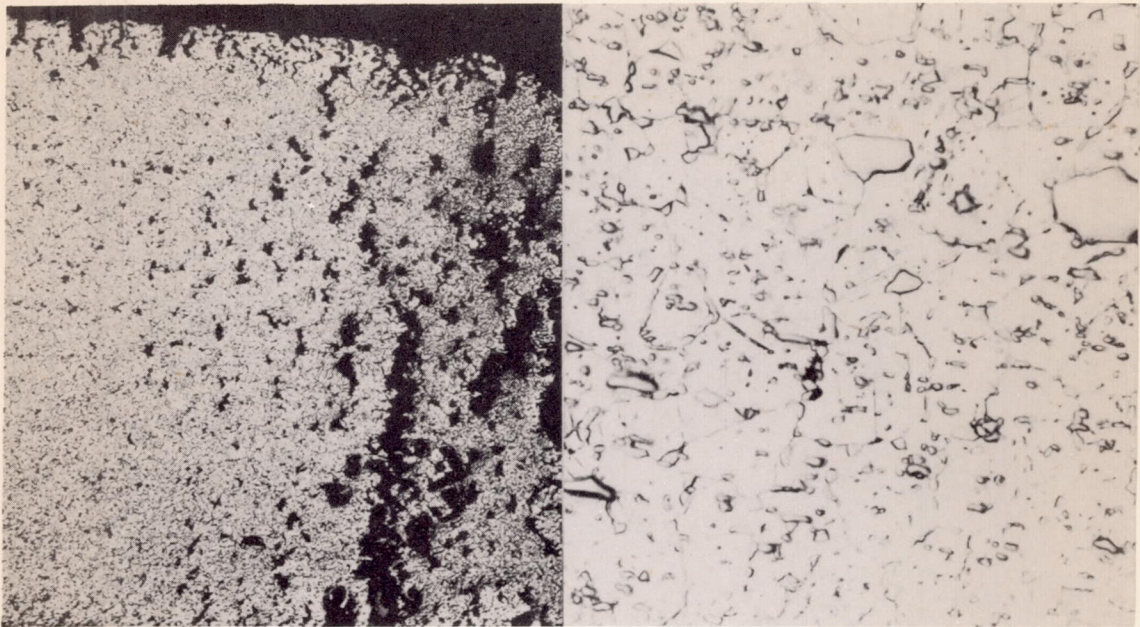

Fracture - 100X

Interior - 1000X

(b) 518 hours for rupture at 1700° F under 4000 psi.

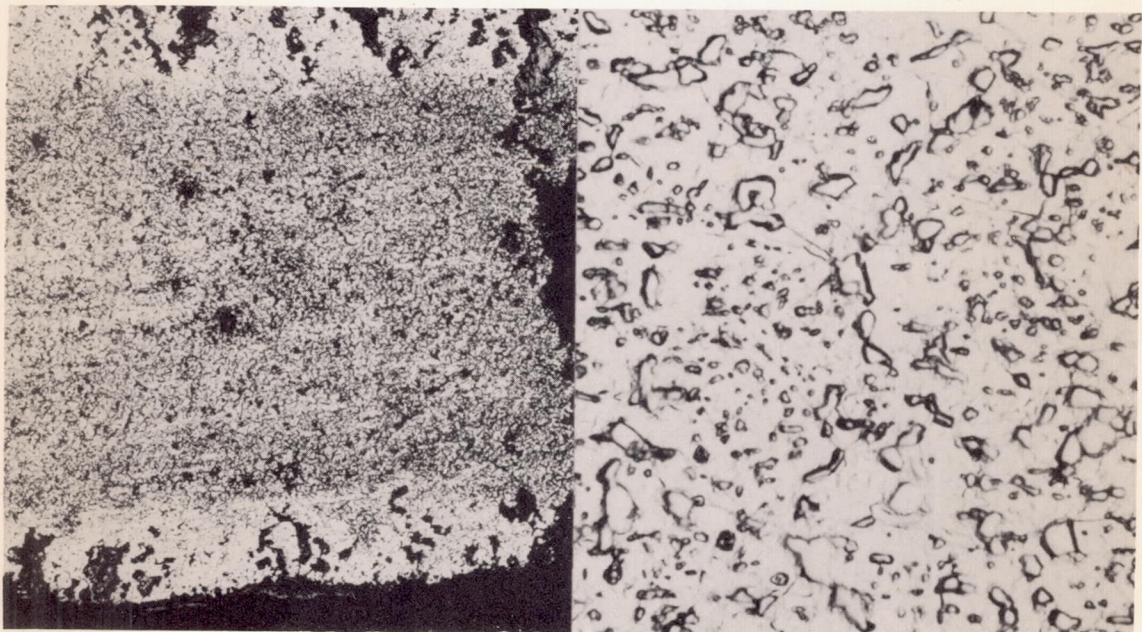


Fracture - 100X

Interior - 1000X

(c) 693 hours for rupture at 1800° F under 2000 psi.

Figure 6.- Concluded.






XXXX - 100X

100X - 100X

XXXX - 100X



100X - 100X

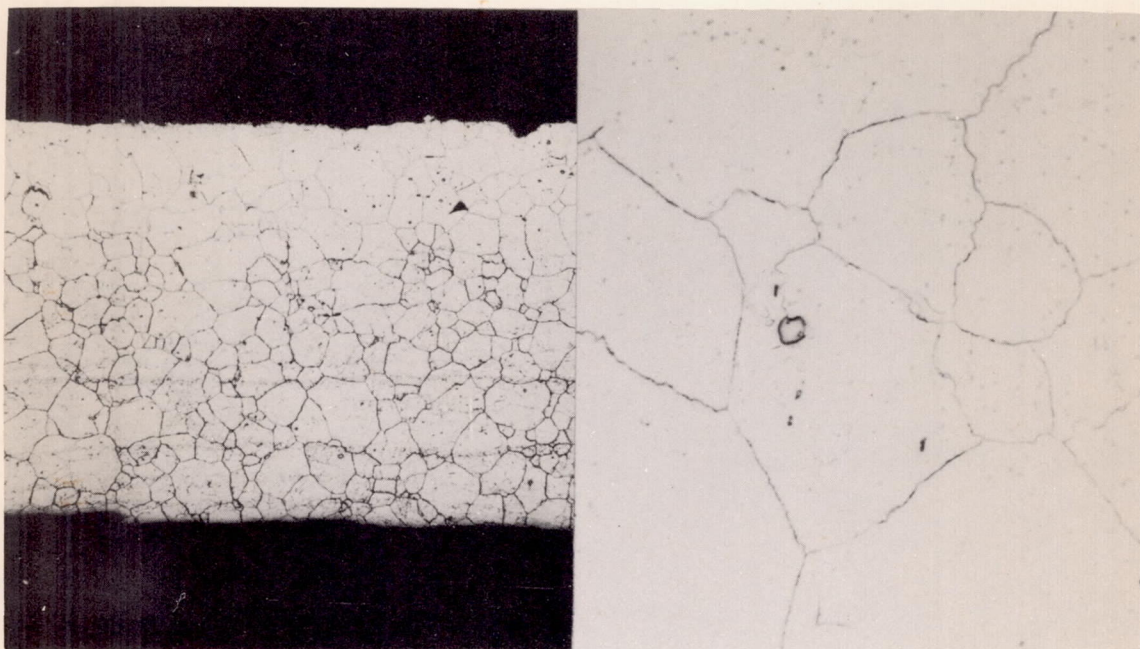

100X

1000X

(a) Original microstructure.

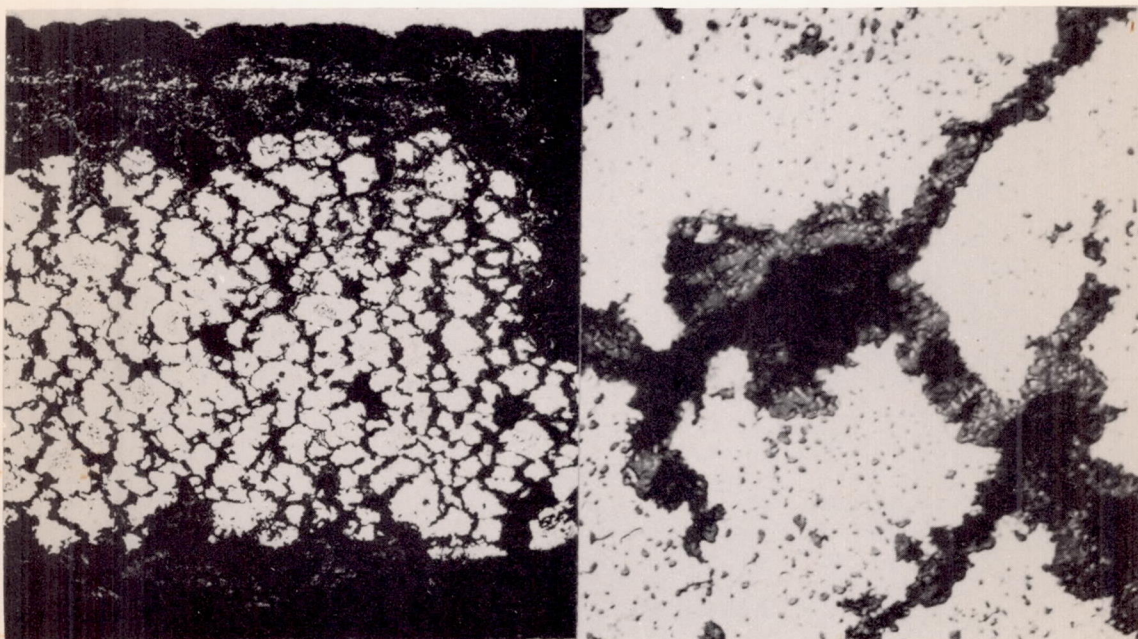

Fracture - 100X

Interior - 1000X

(b) 1492 hours for rupture at 1700° F under 2250 psi.


Figure 7.- Microstructures of sheet Inconel-1 alloy. Electrolytic chromic acid etch.

[Faint, illegible text block]

[Faint, illegible text block]

[Large, faint, illegible text block]

[Faint, illegible text block]


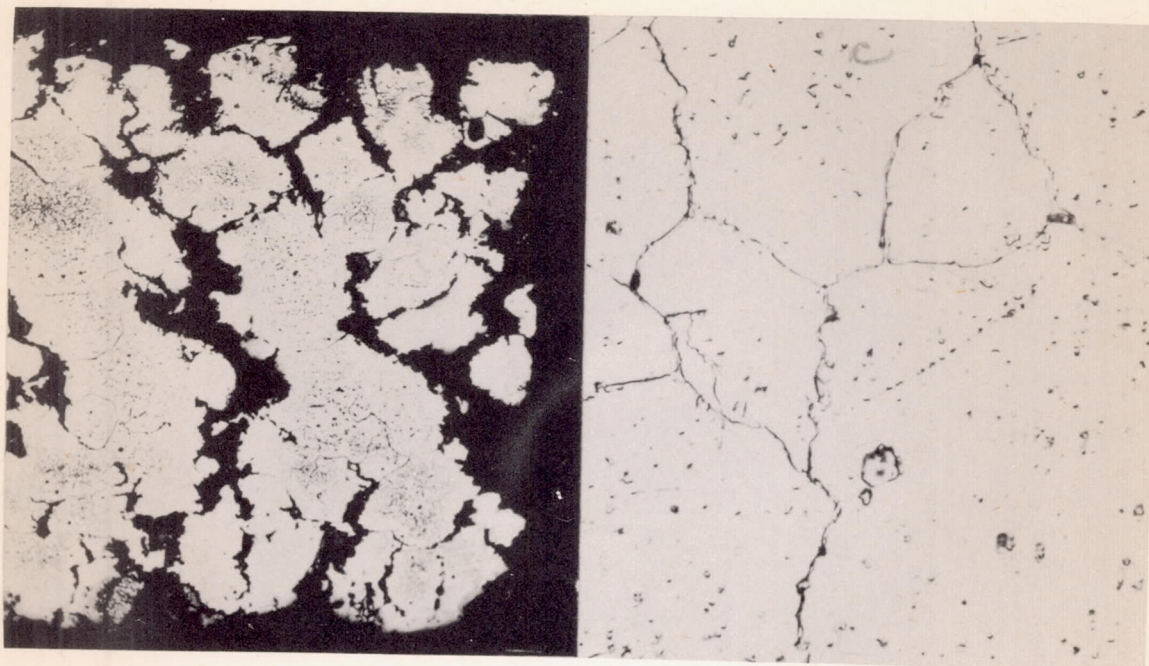


Fracture - 100X

Interior - 1000X

(c) 605 hours for rupture at 1800° F under 1500 psi.

Figure 7.- Concluded.

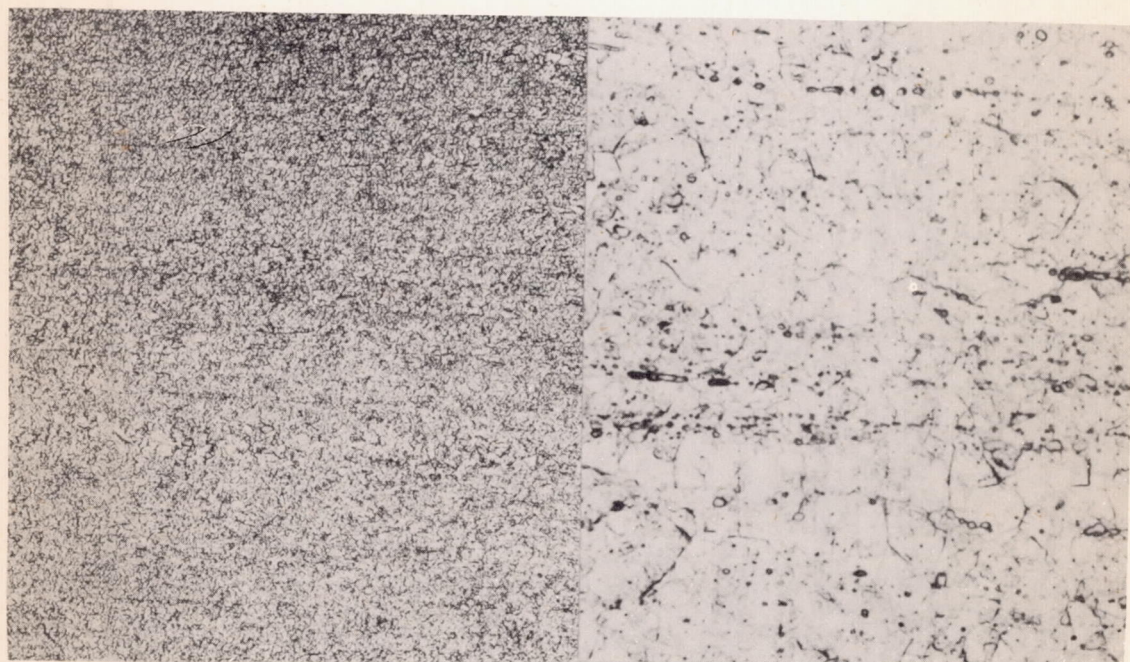


100X

1000X

(a) Original microstructure.

Figure 8.- Microstructures of sheet low-carbon N-155 alloy. Acid ferric chloride etch.




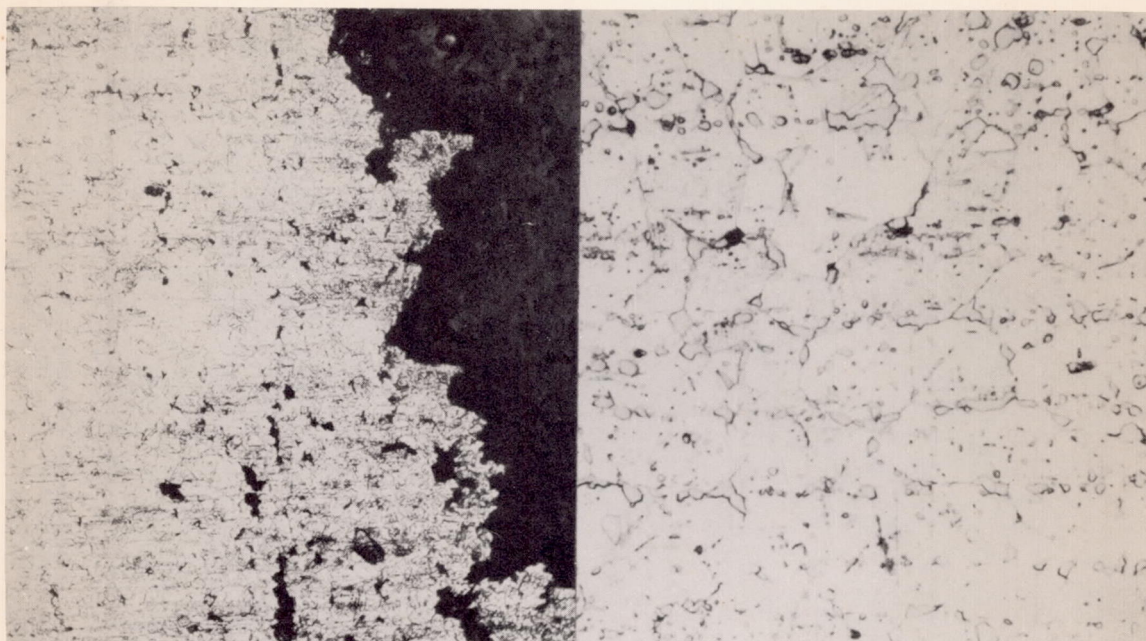

Fracture - 100X

Interior - 1000X

(b) 831 hours for rupture at 1700° F under 4000 psi.

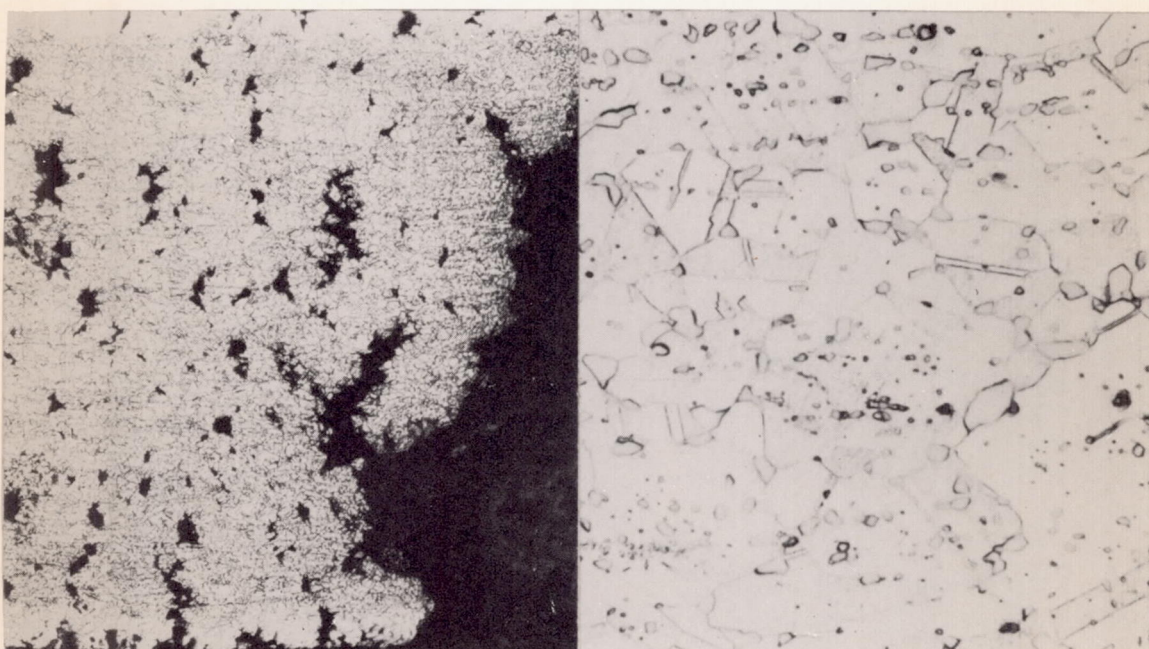



Fracture - 100X

Interior - 1000X

(c) 340 hours for rupture at 1800° F under 2500 psi.

Figure 8.- Concluded.





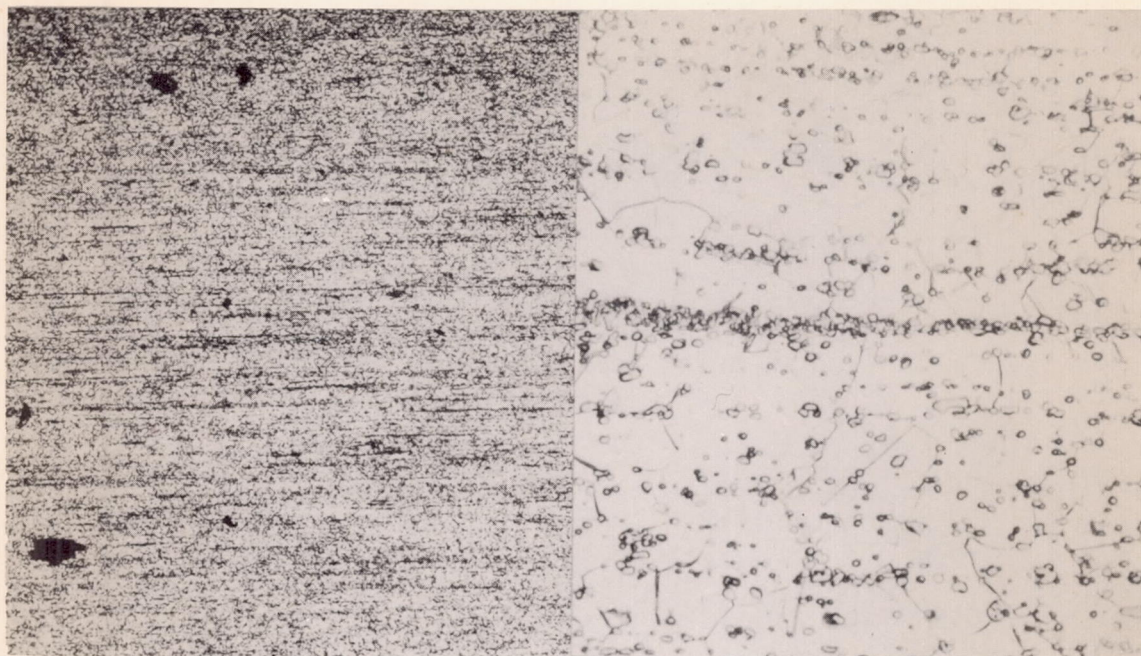

100X

1000X

(a) Original microstructure.

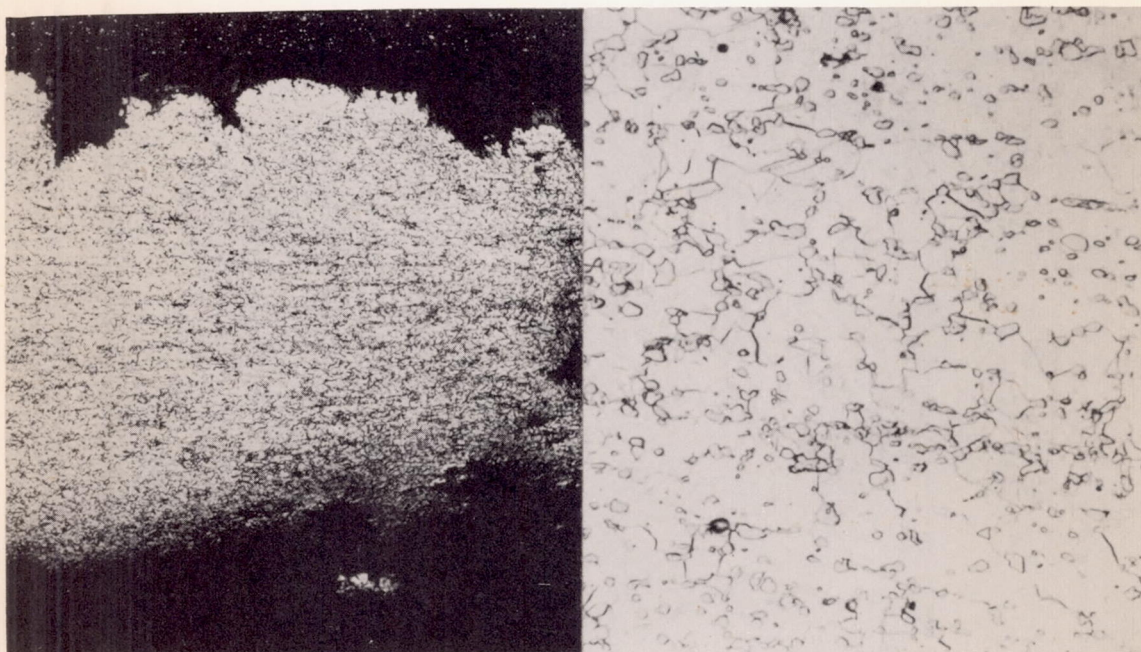



Fracture - 100X

Interior - 1000X

(b) 434 hours for rupture at 1700° F under 5000 psi.

Figure 9.- Microstructures of sheet J-838 alloy. Acid ferric chloride etch.

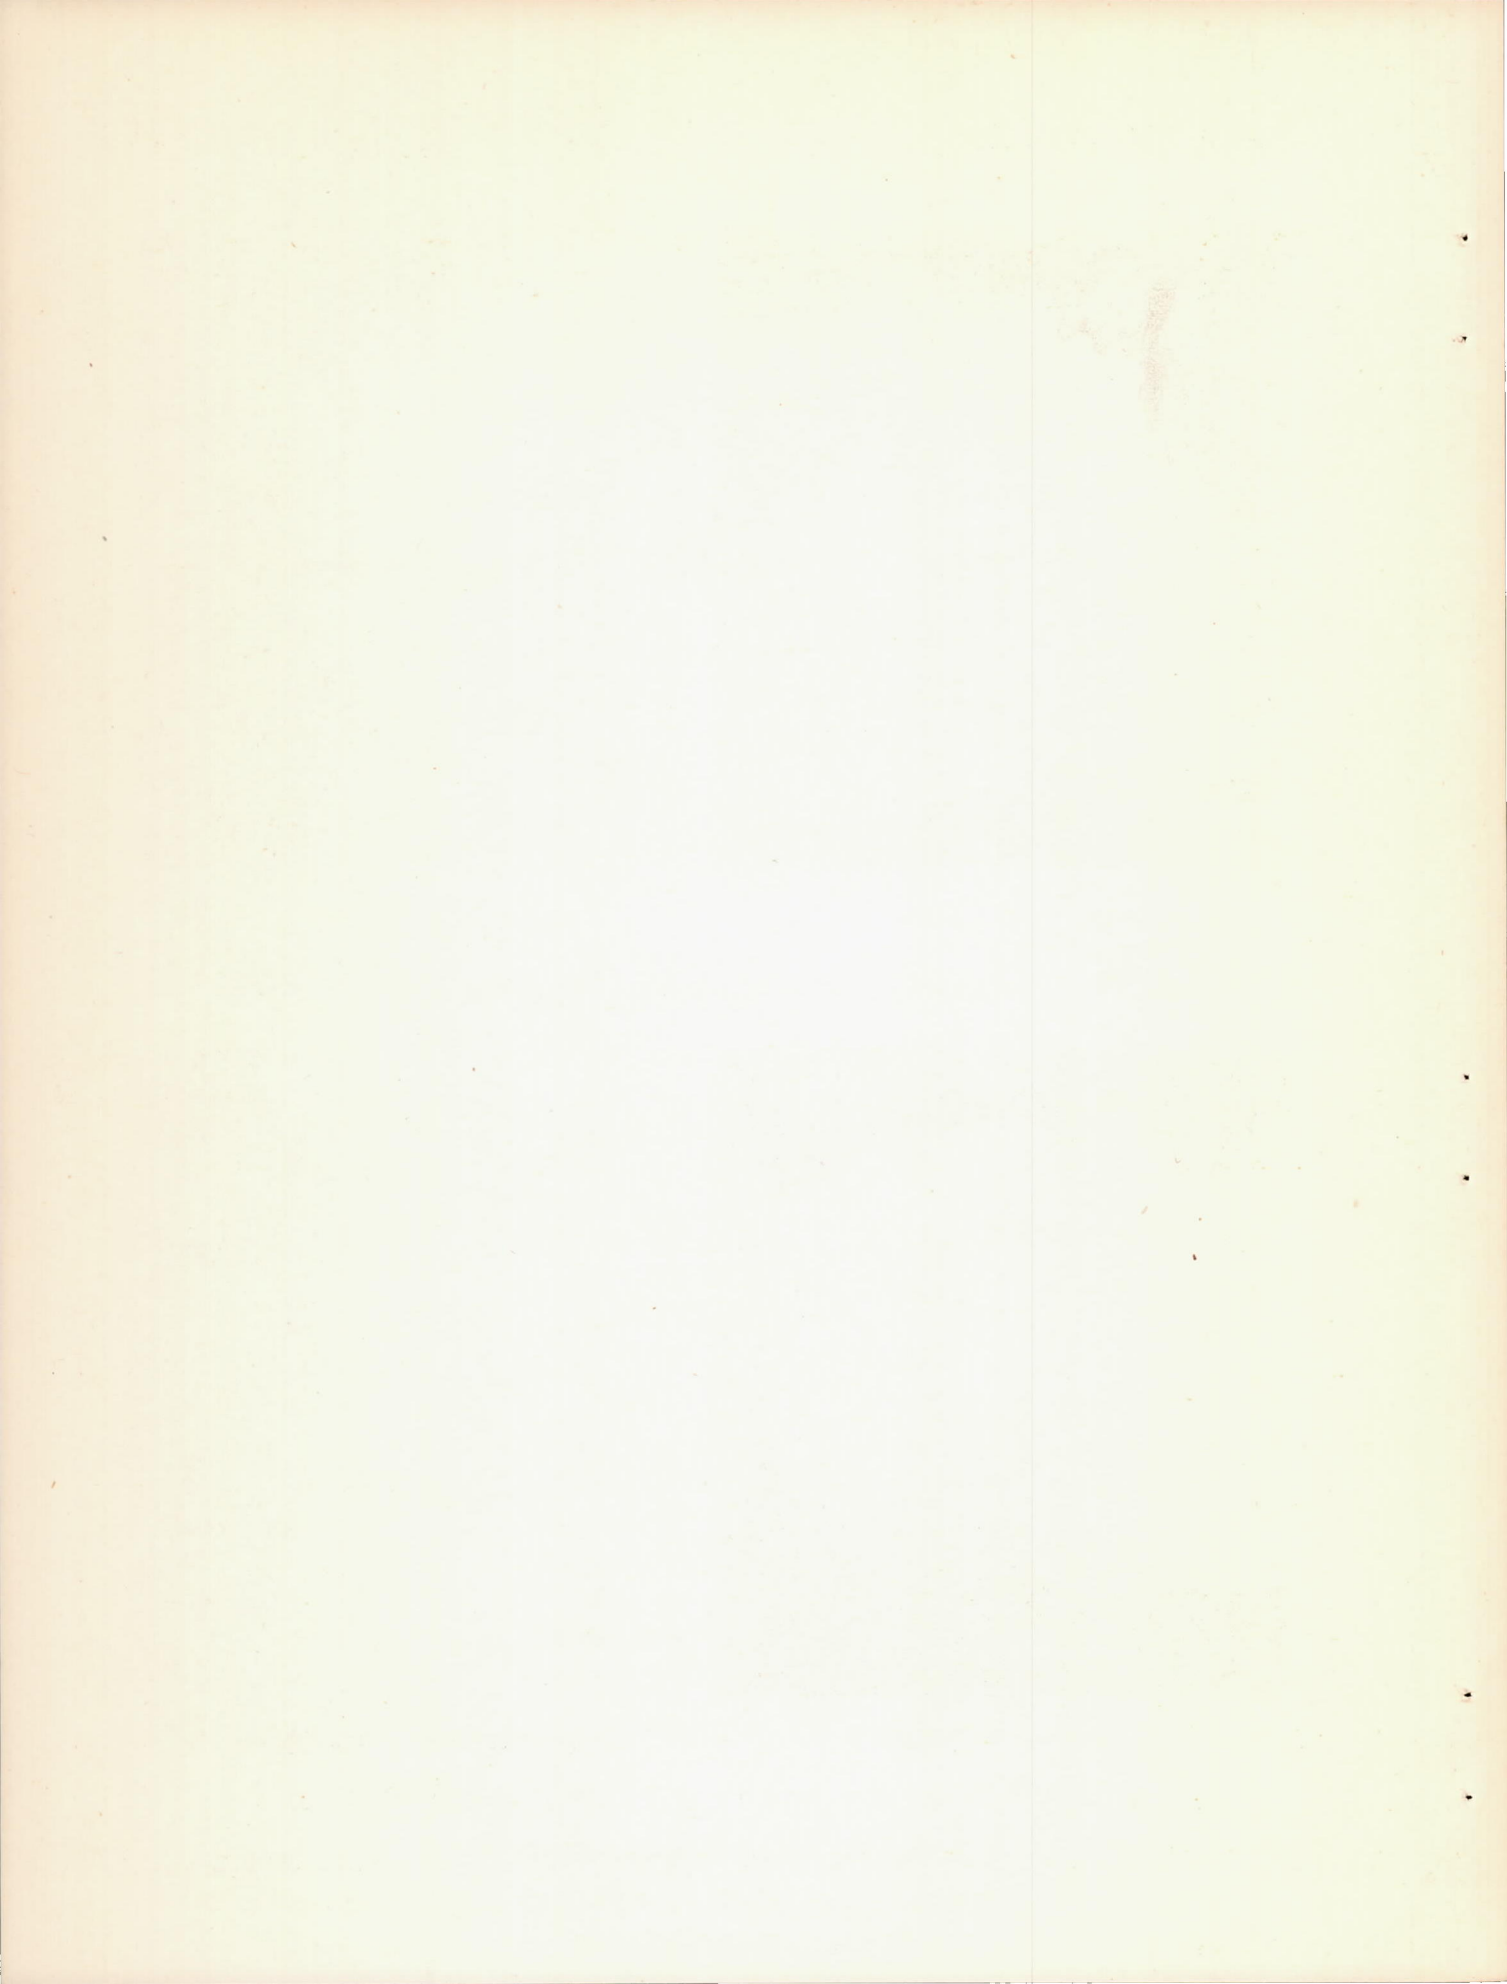


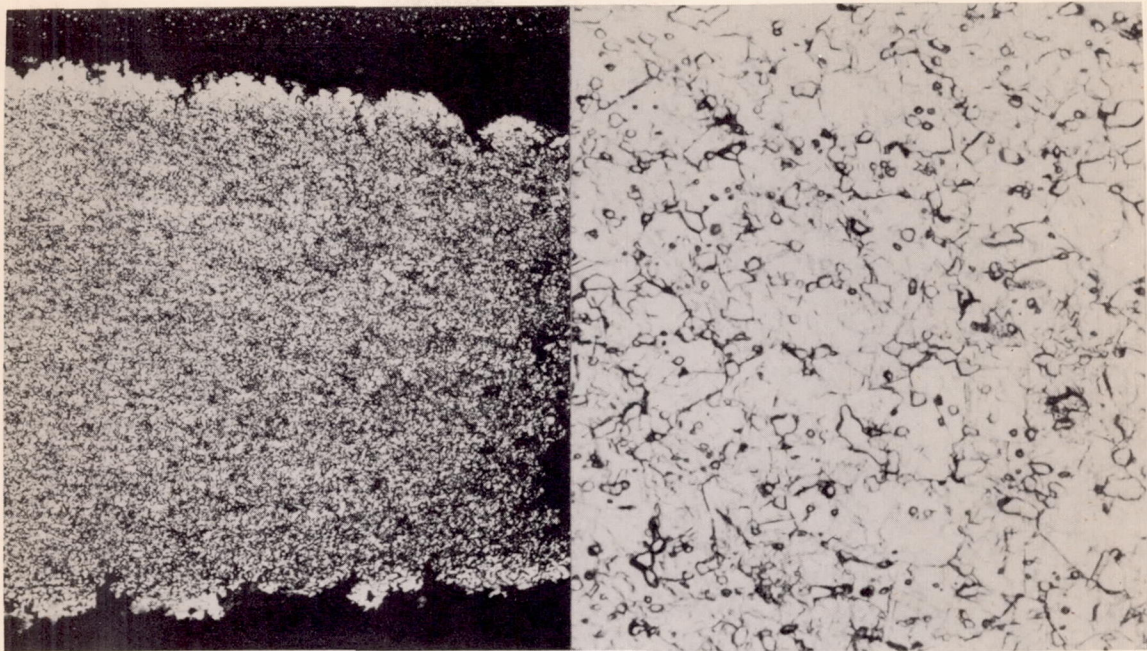


Fracture - 100X

Interior - 1000X

(c) 313.5 hours for rupture at 1800° F under 2500 psi.

Figure 9.- Concluded.

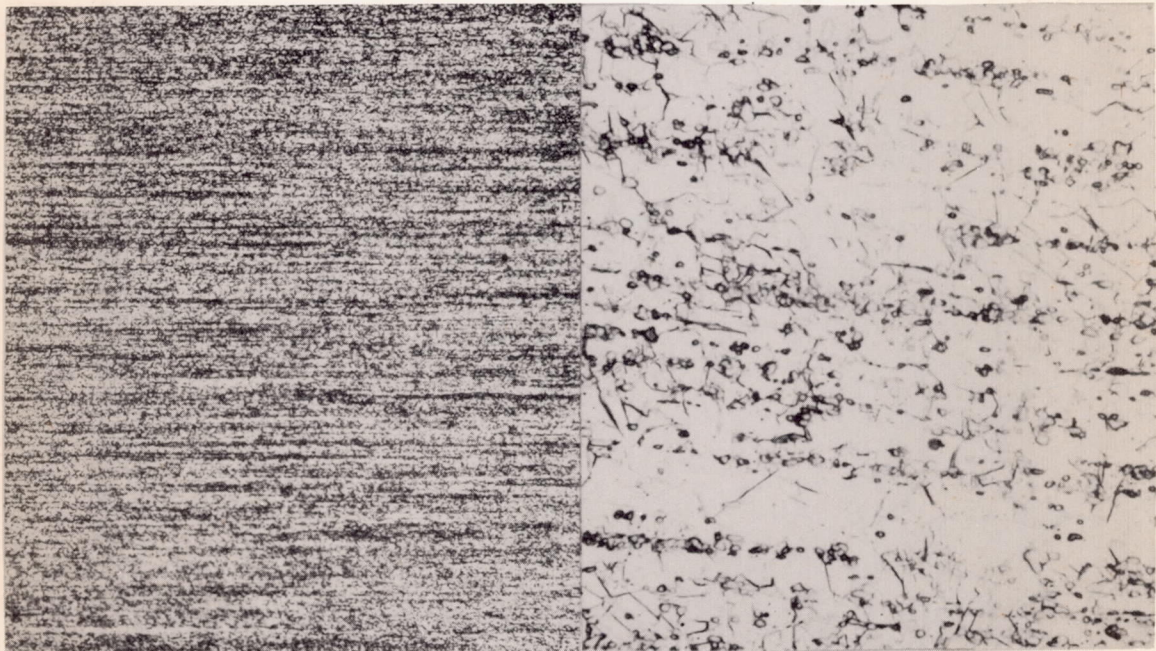


100X

1000X

(a) Original microstructure

Figure 10.- Microstructures of sheet J-840 alloy. Acid ferric chloride etch.




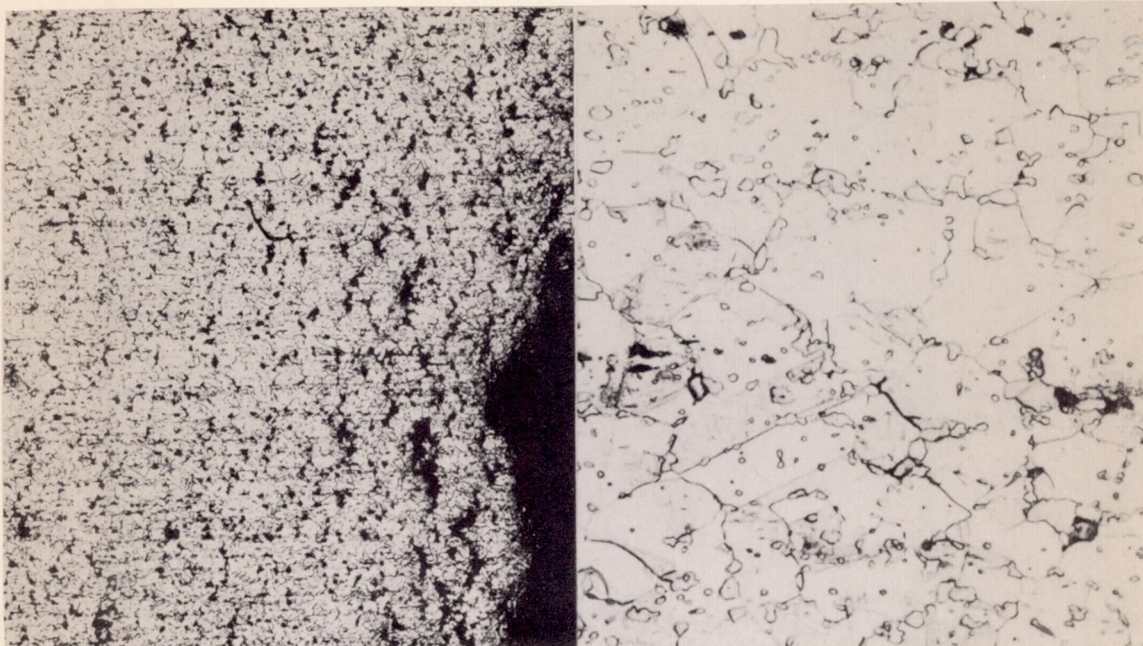

Fracture - 100X

Interior - 1000X

(b) 1133 hours for rupture at 1700° F under 3000 psi.

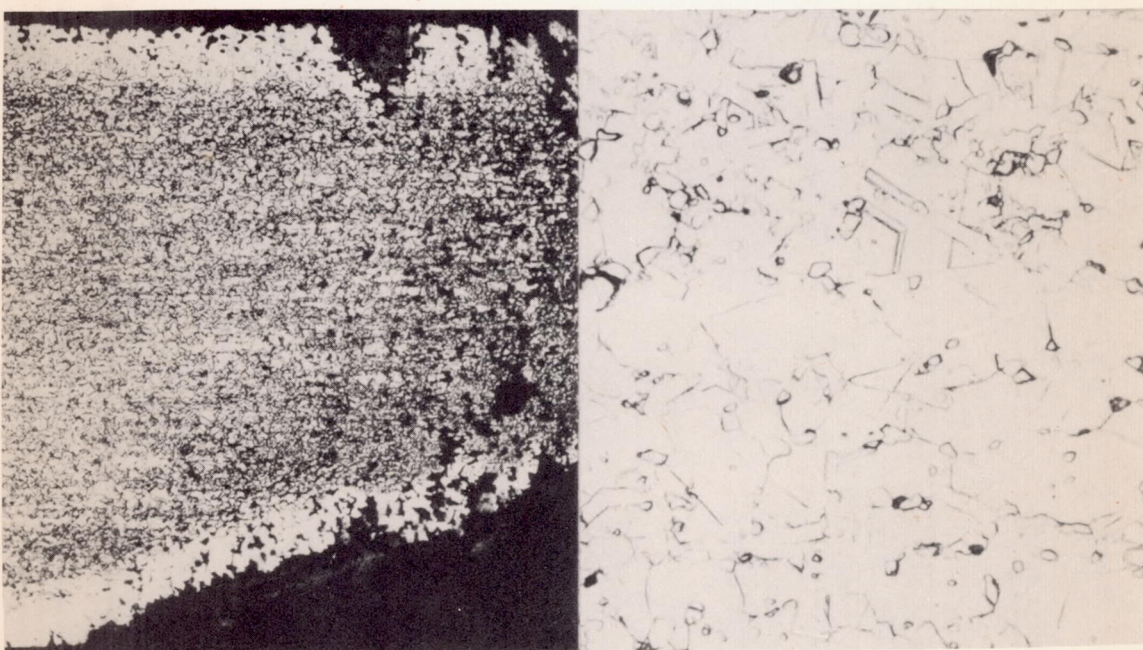



Fracture - 100X

Interior - 1000X

(c) 1309 hours for rupture at 1800° F under 1700 psi.

Figure 10.- Concluded.





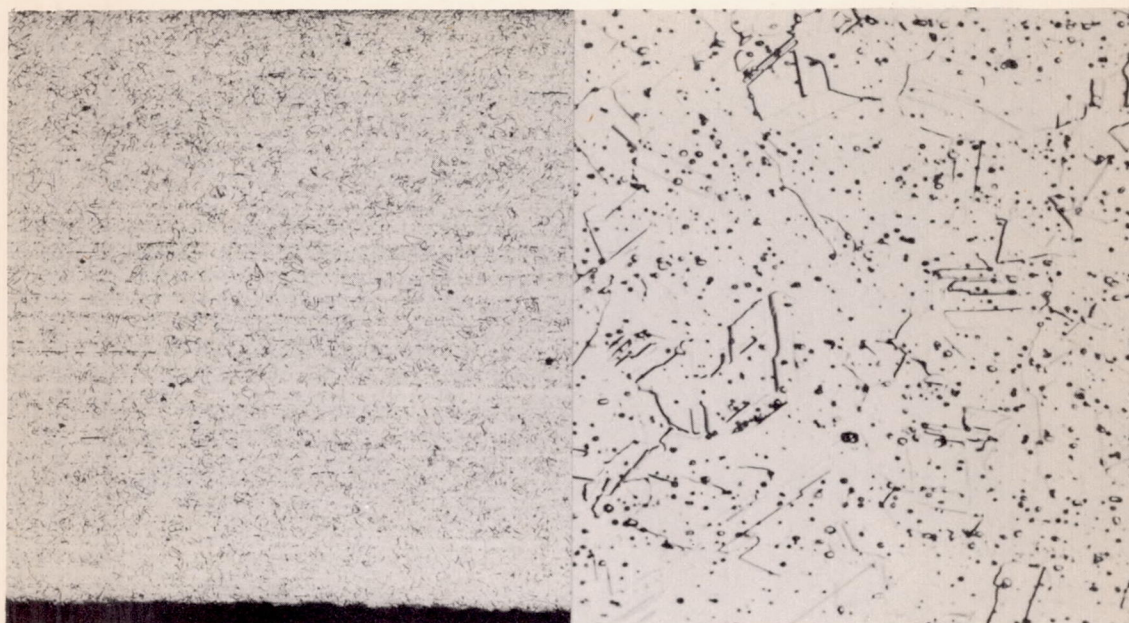

100X

1000X

(a) Original microstructure.

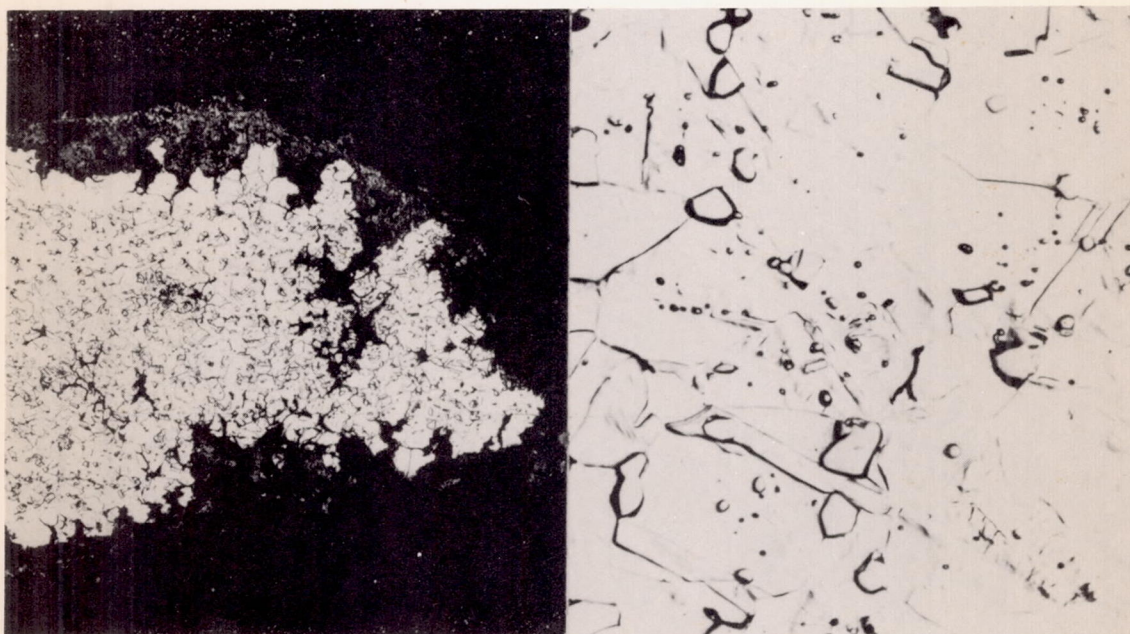


Fracture - 100X

Interior - 1000X

(b) 811 hours for rupture at 1700⁰ F under 1500 psi.


Figure 11.- Microstructures of sheet type 330 alloy (15Cr-35Ni).
Aqua regia in glycerine etch.



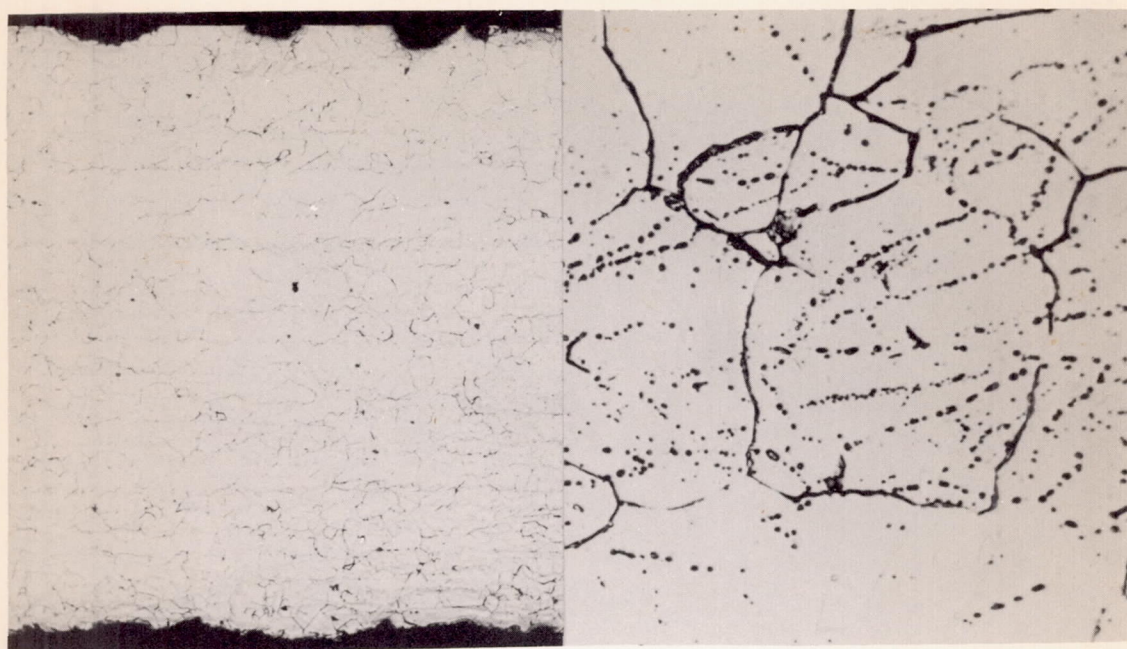


100X

1000X



(a) Original microstructure.

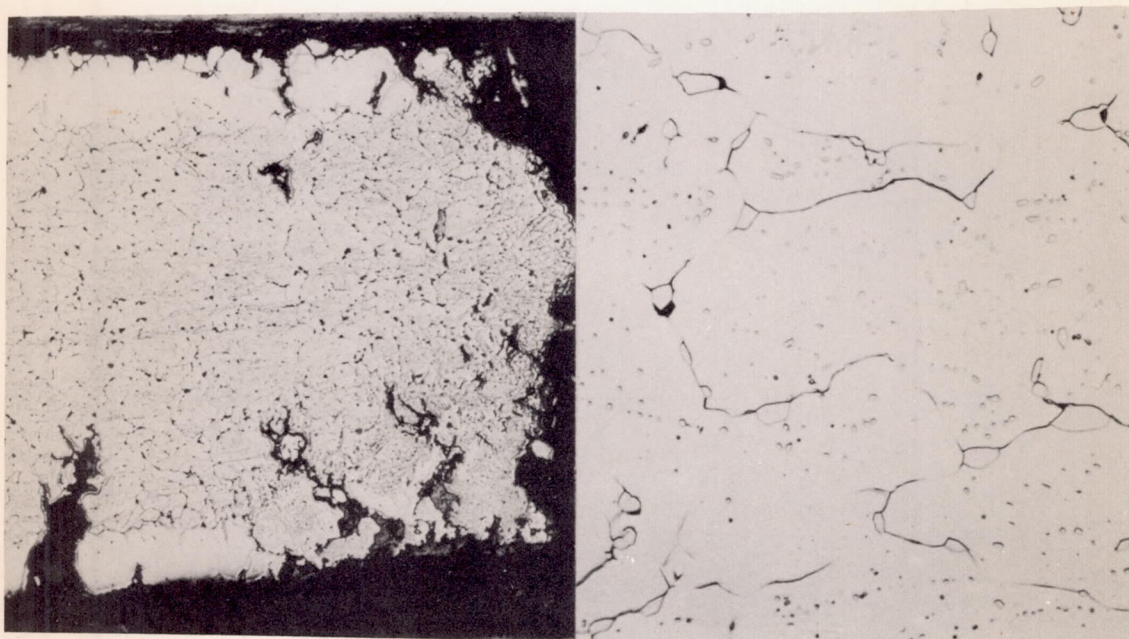


Fracture - 100X

Interior - 1000X

(b) 728 hours for rupture at 1700° F under 2500 psi.



Figure 12.- Microstructures of sheet type 310 alloy (25Cr-20Ni).
Electrolytic chromic acid etch.

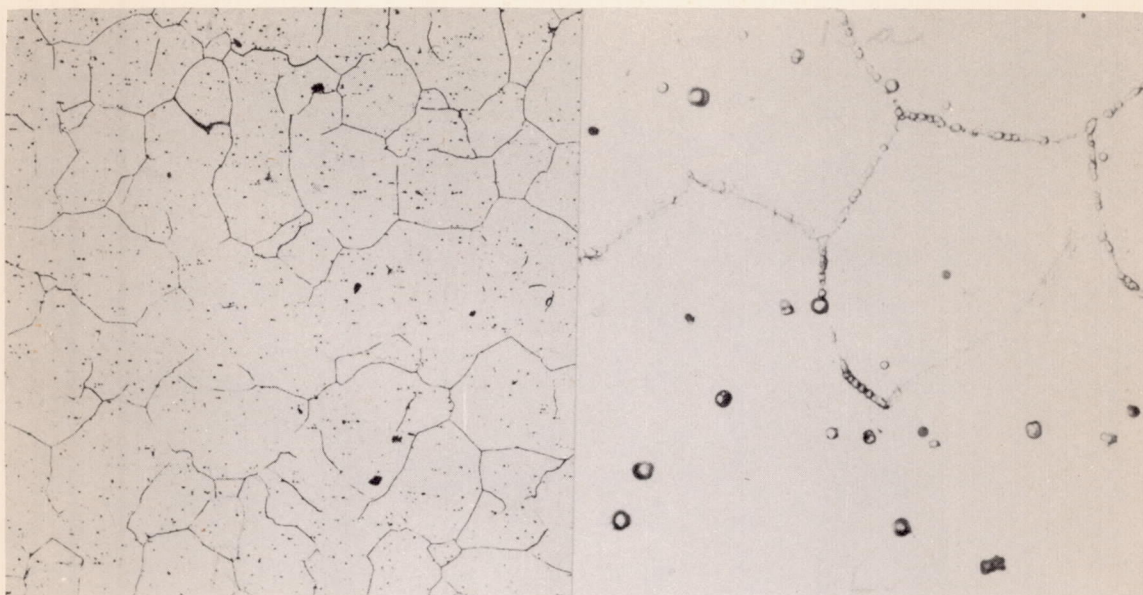

100X

1000X

(a) Original microstructure.

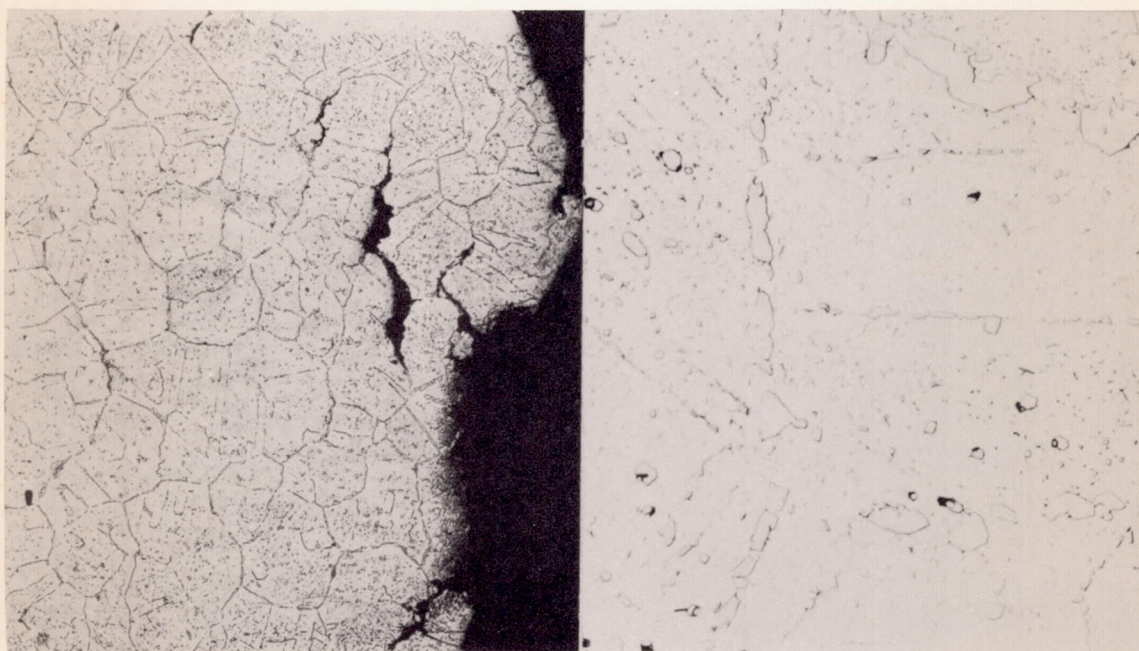


Fracture - 100X

Interior - 1000X

(b) 1124 hours for rupture at 1700^o F under 3000 psi.

Figure 13.- Microstructures of sheet type 310S (AF-18) alloy (25Cr-20Ni+Si). Electrolytic chromic acid etch.


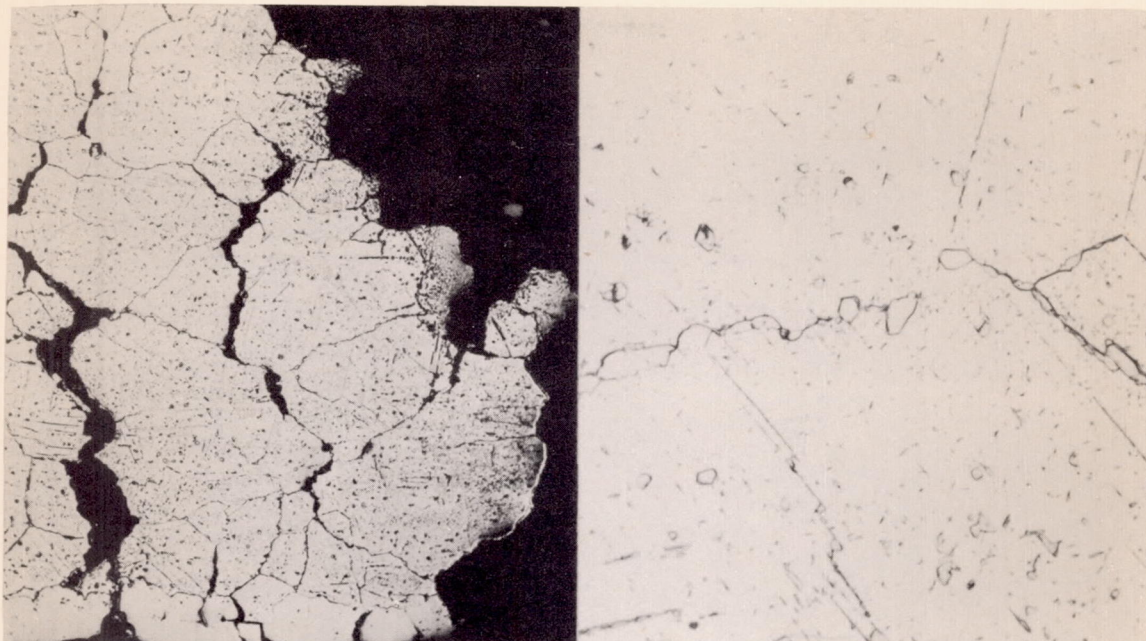


Fracture - 100X

Interior - 1000X

(c) 384 hours for rupture at 1800° F under 2200 psi.

Figure 13.- Concluded.

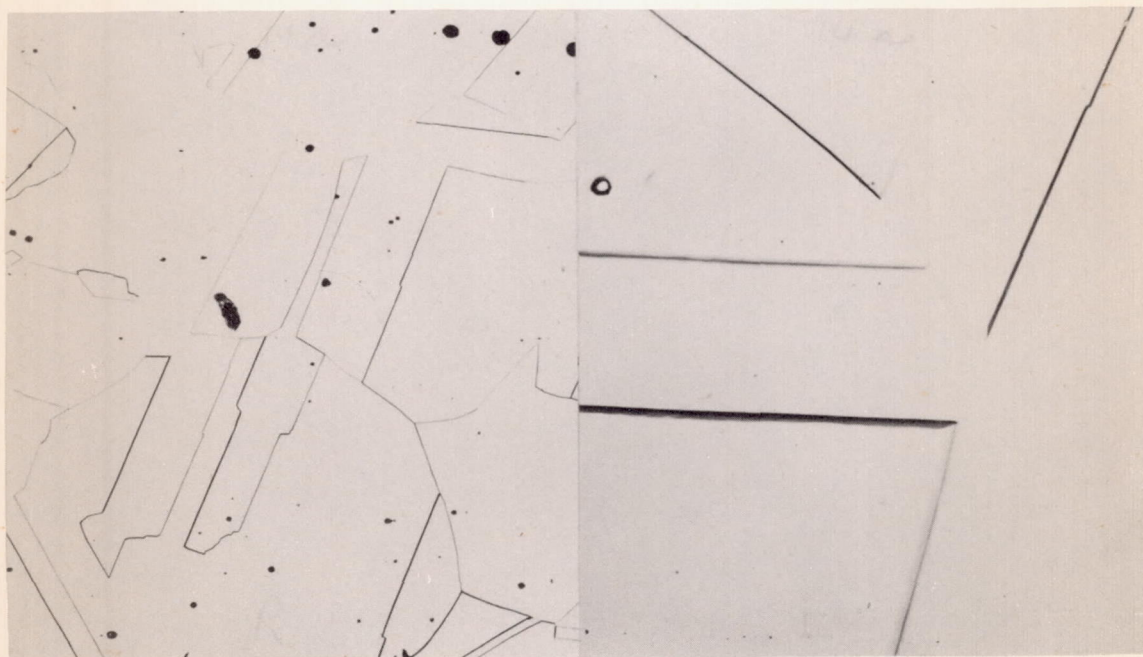

100X


1000X

(a) Original microstructure.

Figure 14.- Microstructures of sheet type 310S (14626) alloy (25Cr-20Ni+Si). Aqua regia in glycerine etch.




[The following text is extremely faint and largely illegible, appearing to be bleed-through from the reverse side of the page. It seems to consist of several paragraphs of text, possibly a letter or a report, with some lines that might be identifiable as "I have the honor to acknowledge the receipt of your letter of the 10th inst." and "Very respectfully, your obedient servant, J. M. Smith".]

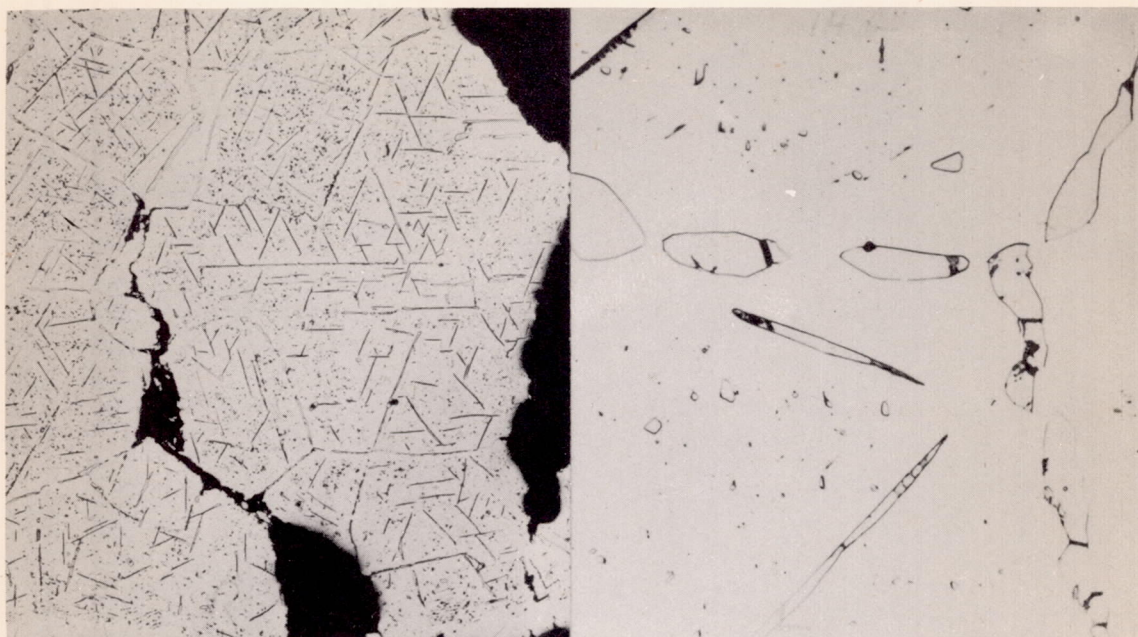

Fracture - 100X

Interior - 1000X

(b) 397 hours for rupture at 1700° F under 2400 psi.

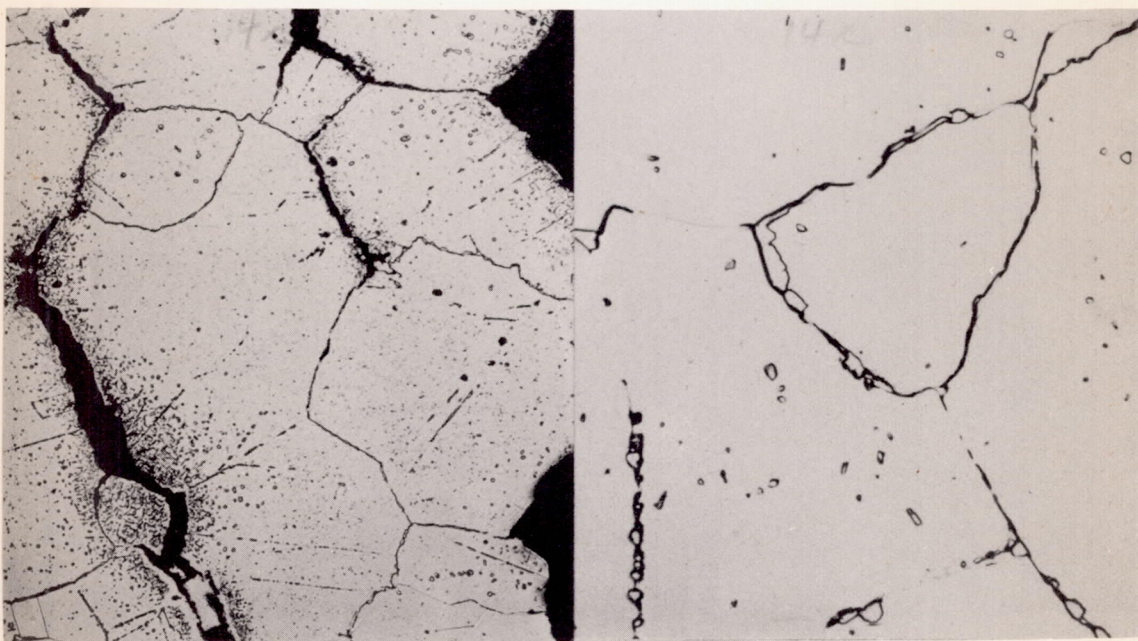


Fracture - 100X

Interior - 1000X

(c) 569 hours for rupture at 1800° F under 1700 psi.

Figure 14.- Concluded.




10000 - 10000
 10000 - 10000

10000 - 10000
 10000 - 10000

NACA



Figure 10 - Comparison

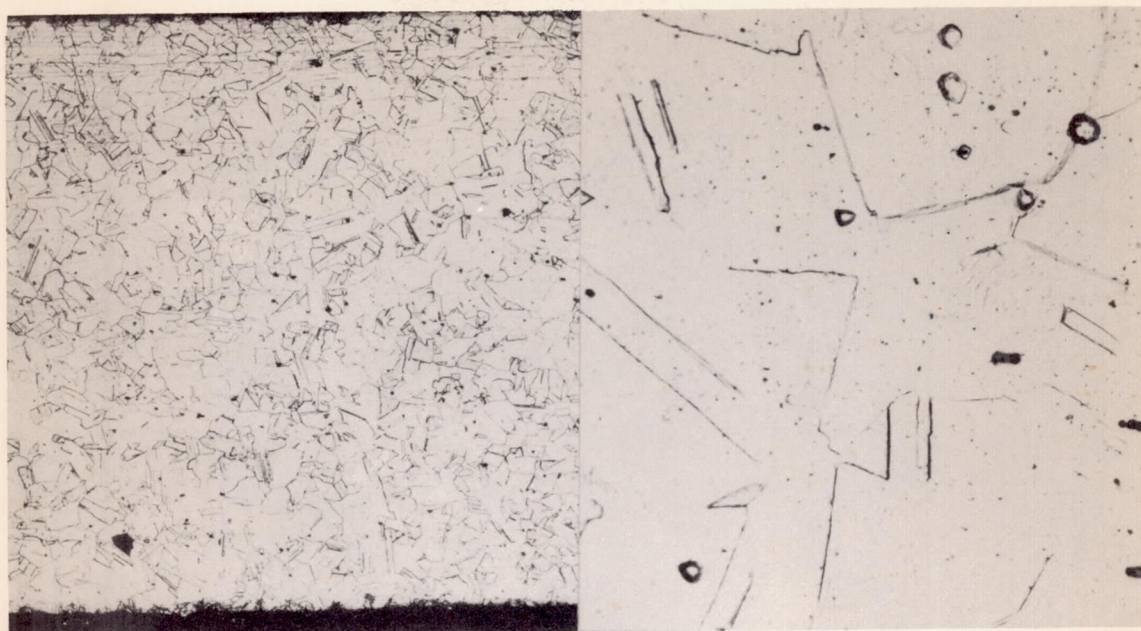

100X

1000X

(a) Original microstructure.

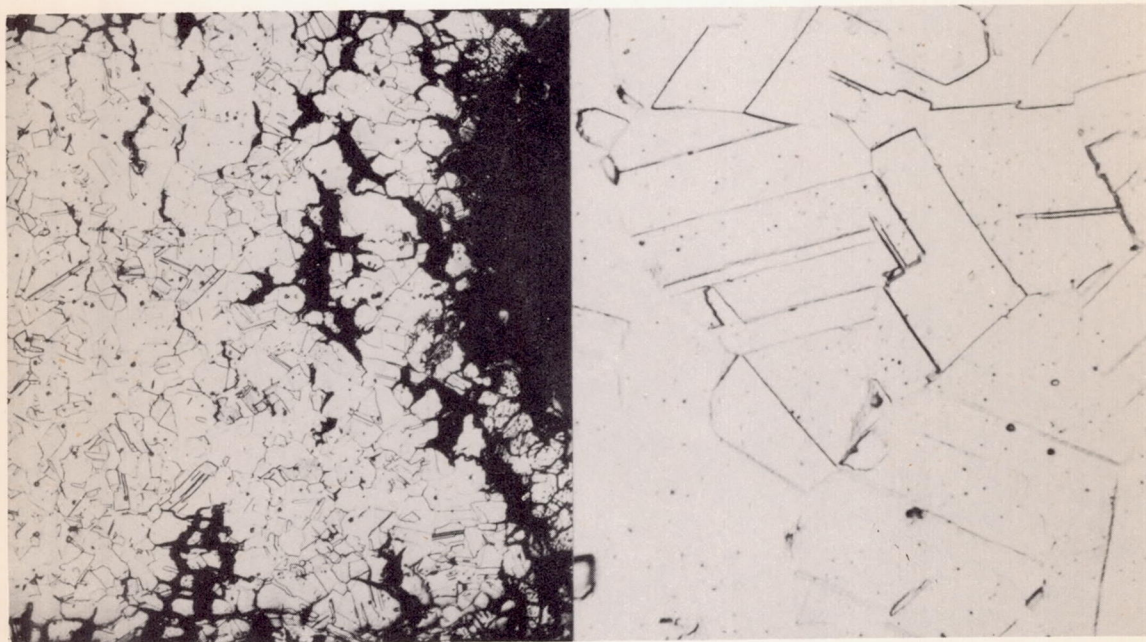

Fracture - 100X

Interior - 1000X


(b) 277 hours for rupture at 1700° F under 2500 psi.

Figure 15.- Microstructures of sheet type 309 alloy (25Cr-12Ni).
Electrolytic chromic acid etch.


THE NEW YORK PUBLIC LIBRARY

ASTOR LENOX TILDEN FOUNDATION


500 N. 4TH ST. NEW YORK, N. Y. 10017

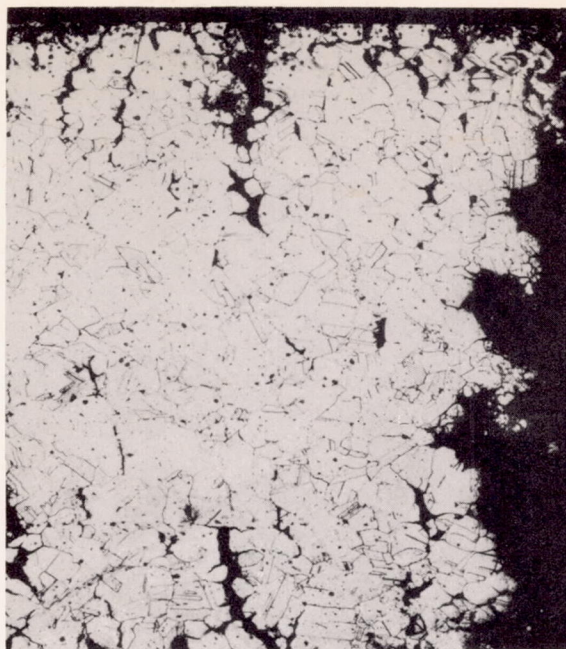

Fracture - 100X

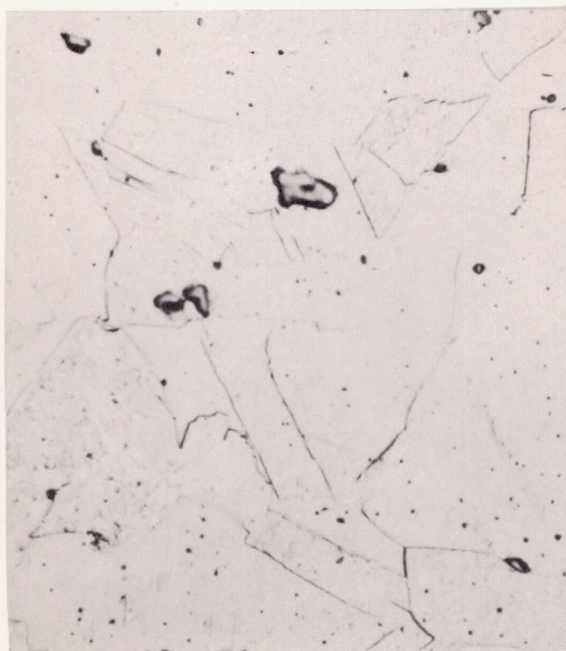


Interior 1000X



(c) 321 hours for rupture at 1800° F under 1800 psi.

Figure 15.- Concluded.

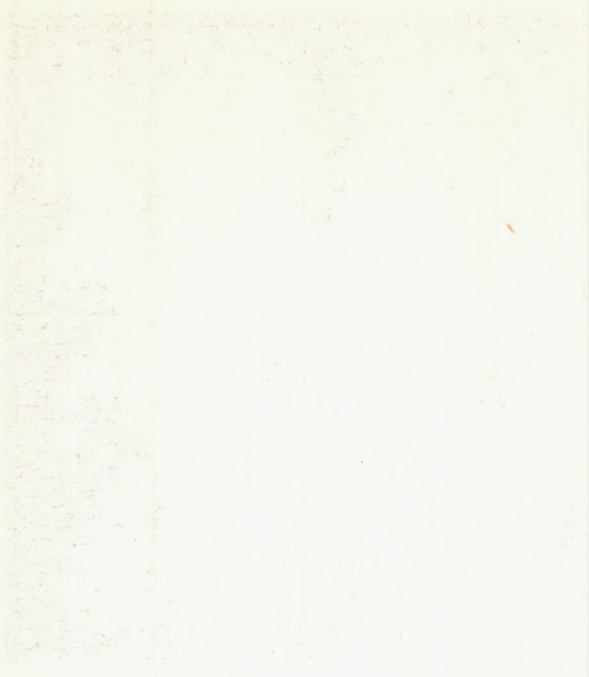

(0011 00110000 00 00000000)